

Abcite[®]

Marine and Offshore



Certified protection for marine and offshore structures

Coatings for parts and components used in offshore environments have to fulfill very stringent requirements.

High humidity and saline air in combination with intensive UV radiation create a highly corrosive environment. At the same time the coating is exposed to extreme mechanical stress in the splash zone.

Abcite® has proved its worth for many years under these conditions. A unique one layer, primer-less coating which fulfills the highest corrosion requirements and can replace up to 6 layers of conventional protective coating - all in one!

Maintenance-free for reduced costs and extended service life

- Superior corrosion resistance, UV & salt spray resistance: C5-M high according to ISO 12944-6 and C5-M according to ISO 20340
- Impermeable barrier even in permanent immersion or condensation
- Suitable for extreme climate conditions: from -60°C to +75°C
- Durable adhesion to steel, even in hot water
- Excellent chemical resistance to most kinds of water
- Reduced bacterial growth and fouling
- Superior resistance to cavitation and abrasion
- Reduced friction of water flow, reducing pressure drop

Easy to apply and robust

- Coat interior and exterior in one step
- Spray on preheated steel or dip in fluidized bed
- No primer needed (self-adhering film)
- Lower process temperature than nylon coatings
- Excellent edge coverage
- Outstanding impact resistance preventing handling damage
- Easy repair of coating defects
- Excellent color stability over time

Safe and clean



- Free of bisphenols, VOCs and halogens
- No PVC, no phthalates, no plasticizers
- Preserves water quality

Application examples

- Suction pipes and other piping on dredging boats
- Railings, valves and fittings on chemical tankers
- Ladders, balustrades and metallic structures exposed to marine climate
- Immersed metallic structures or structures in splash zone
- Port infrastructure
- Fire lines on offshore or marine infrastructure



Product features

Abcite® 1060 / Abcite® X60		
Film thickness	Min. 300 µm	
External application - weathering resistance	Yes	
Service temperature	From -60 °C to 75 °C	
Application method - on preheated surface	Spraying Abcite® X60	Fluidized bed Abcite® 1060
		
Overcoating with decorative powder possible	Yes	
Colors	Blue RAL 5012 and RAL 5017 Green RAL 6005 Grey RAL 7001 and 7016 Black RAL 9005 White RAL 9016*	
Durability of coated product	Active references in use for more than 20 years without any maintenance	

*Other colors upon request

Abcite®, a proven and reliable coating solution for the most demanding environments

Since 1999, Abcite® 1060 and X60 are used to protect dredging ships built by Royal IHC. Jet water pipes, inboard suction pipes and various other water pipes remain fully protected and maintenance-free since the ships commissioning. Boskalis, DEME, Van Oord, Royal Huisman, Meyer Werft and Thyssen Krupp are some of the names on the long list of Abcite® users.

Voice of the customer

Jeroen Klijn
Technical Director
Stout Pijpleidingen BV

"We are using Abcite® for many years as repair solution for the pipes installed on vessels. Old corroded pipes will be replaced by new ones protected by Abcite®.

The outstanding properties of Abcite®, its chemical and abrasion resistance for instance, allow us to offer our customers a long term and maintenance free protection, which is an invaluable benefit for the marine industry.

We are convinced, that Abcite® is the perfect solution for us and our customers, for an excellent and durable corrosion protection."



Axalta Polymer Powders Switzerland Sarl

25 rue Saint Joseph

CH-1630 Bulle

Tel: +41 26 913 09 10


Fax: +41 26 913 01 99

Abcrite-info@axaltacs.com

Your local contact can be found at:

www.polymerpowders.axaltacs.com

Your Abcrite® partner

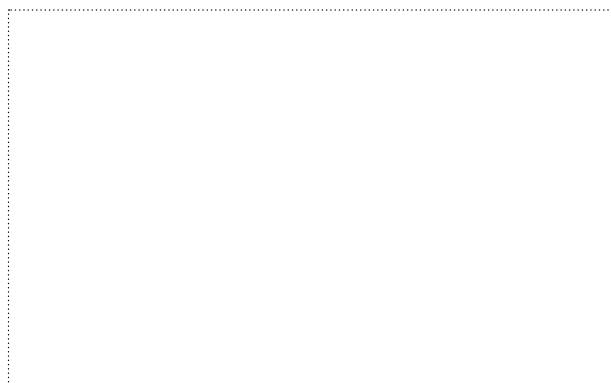

Abcite[®]

Water Infrastructure



Durable and sustainable corrosion protection

Abcite® provides enhanced surface protection for:

- Pipes, fittings, filters, flanges, valves and tanks in contact with water and waste liquids
- Pumping stations, distribution systems, desalination plants, waste water treatment plants, etc.

Safe and clean

- Free of all bisphenols, VOCs and halogens
- No PVC, no phthalates, no plasticizers
- Preserves water quality
- Controlled, tested and certified to the most stringent standards for contact with potable water

Maintenance-free for reduced costs and extended service life



- Impermeable barrier, even in case of permanent immersion or condensation
- Durable adhesion to steel, even in hot water
- Not affected by sea water or most chemicals present in wastewater
- Excellent chemical resistance to usual water disinfection agents
- Reduced bacterial growth and fouling
- Superior resistance to cavitation and abrasion
- Reduced friction loss

Simple and robust

- Coat interior and exterior in one step
- Spray or dip in fluidized bed on preheated steel
- No primer, self-adhering monofilm
- Lower process temperature than nylon coatings
- Excellent edge and corner coverage
- Outstanding impact resistance preventing handling damage
- Easy repair of coating defects



Product features

Abcite® 1060 / Abcite® X60		
Film thickness	Min. 300 µm	
External application - weathering resistance	Yes	
Application method - on preheated surface	Spraying Abcite® X60	Fluidized bed Abcite® 1060
		
Overcoating with decorative powder possible	Yes	
Colors	White RAL 9016, Blue RAL 5012, Blue RAL 5017, grey RAL 7001, Other colors upon request	
Long term durability of coated product	Active references in use for more than 20 years without any maintenance	

Abcite®, a proven solution for more than 20 years

- Replacing epoxy coatings since 1995 in major potable water plants in Belgium (De Watergroep, AWW, Farys, Pidpa, Vivaqua).
- Kwinana desalination plant, supplying the Perth metropolitan area (Australia) with 140'000 m³ drinking water per day using reverse osmosis. Abcite® X60 is used since 2006 to protect pre-filters.
- Swimming pool in Antwerp Belgium: handrails, balustrade and steps protected with Abcite® X60 since 2010.
- Abcite® 1060 protects pipes and accessories on dredging ships since 1999 (DEME, Boskalis, Van Oord).



Voice of the customer

Ing. Jos Robeyns
Head of material technology department at De Watergroep,
Brussels (Belgium):

"We have adopted Abcite® 1060 and X60 since 2001 for water supply systems, including potable water production plants, water towers, tanks and distribution stations, with full satisfaction.

In addition to its excellent abrasion resistance and high electrical insulation, this tough coating can absorb all inevitable impacts occurring on construction sites and prevent installation damage.

The first systems coated 14 years ago are still intact today, which demonstrates the outstanding durability of this coating."



Approvals*:

- NSF/ANSI 61 (USA)
- KTW and DVGW (Germany)
- WRAS (UK)
- AS/NZS 4020 and 4158 (Australia and New Zealand)
- ACS Attestation de Conformité Sanitaire (France)
- Belgaqua Hydrocheck (Belgium)



* Certificates valid for certain colors. Please contact your Axalta Coating Systems representative for additional information



Axalta Polymer Powders Switzerland Sarl

25 rue Saint Joseph

CH-1630 Bulle

Tel: +41 26 913 09 10


Fax: +41 26 913 01 99

Abcrite-info@axaltacs.com

Your local contact can be found at:

www.polymerpowders.axaltacs.com

Your Abcrite® partner

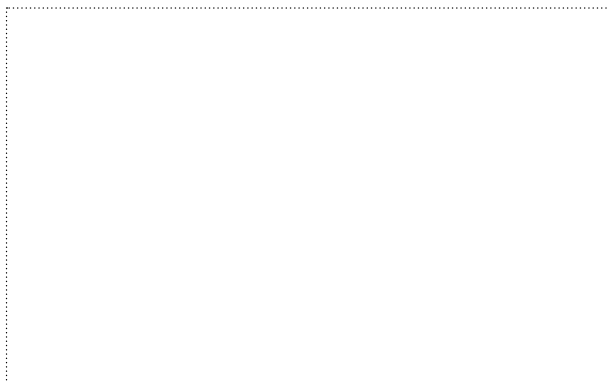

Abcite®

Outdoor furniture



Tough coating for all weather conditions

Enhanced corrosion protection for outdoor furniture, lighting columns, sign poles, benches and fences.

Urban furniture is extremely vulnerable to corrosion caused by acid rain, air pollution, road salt, high temperature variations, condensation and, in cities and towns, dog fouling. Damage is even more severe at sea side, where sun, salt, wind and humidity attack the metal very aggressively.

The lower part of furniture is particularly exposed to salt and dog fouling – and must withstand higher mechanical stress as well.

Once corrosion starts, it is virtually impossible to stop. Replacing the asset is the only alternative to prevent its eventual collapse, **unless you protect it from the beginning with Abcite®!**

Abcite® is the solution!

- Superior corrosion resistance: C5-M and Im3 High according to ISO 12944-6
- High impact and abrasion resistance
- UV stability
- Excellent chemical resistance (pH 1 to 12)
- Protects galvanized substrates from erosion
- Soft touch
- One-coat process: no primer required
- Environmentally friendly (no VOC, halogen free, BPA free)
- On site repairable
- Can be overcoated with Alesta® powder coatings for decorative purposes

Benefits

- Maintenance free over the entire product lifetime
- Resistant to all climate conditions
- Color stability over time
- No corrosion, even on damaged furniture
- Easy to clean, even graffiti
- Prevents bacterial growth
- Electrical insulation
- Noise reduction





Product features

Abcite® 1060 / Abcite® X60

The toughest solution

Abcite® 500 / Abcite® 500ES

The best price / performance alternative

Film thickness	Min. 300 µm	
External application - weathering resistance	Yes	
Service temperature	From -60°C to 75°C	
Application method - on preheated surface	<div>Spraying Abcite® X60 - 500ES</div> <div></div>	<div>Fluidized bed Abcite® 1060 - 500</div> <div></div>
Overcoating with decorative powder possible	Yes	
Colors	<div>Blue RAL 5012 and RAL 5017</div> <div>Green RAL 6005</div> <div>Grey RAL 7001 and 7016</div> <div>Black RAL 9005</div> <div>White RAL 9016</div> <div>Other colors upon request</div>	<div>Beige RAL 1001</div> <div>Blue RAL 5017</div> <div>Green RAL 6005</div> <div>Grey RAL 7001 and 7016</div> <div>Black RAL 9005</div> <div>Stainless steel RAL 9006</div> <div>White RAL 9016</div> <div>Other colors upon request</div>
Long term durability of coated product	Active references in use for more than 20 years without any maintenance	
For thin steel and aluminum profiles combining different strengths or thicknesses, we recommend Abcite® 545 / Abcite® X45: the specific viscosity of this product allows to evenly cover all difficult parts and designs.		



1996



2014



Noordbrug Kortrijk Bridge



before



after



Göteborg Energi cable cabinets

Abcite®, a proven solution for more than 20 years

1 Still looking new after almost 20 years

This 80 meter-long and 180 centimeter-high fence in Antwerp was coated with Abcite® in 1996 and looks brand new, still today! No maintenance, no damages, no corrosion for almost 20 years!

2 The most effective long term solution

In 2010, the welded grilles of the Noordbrug Kortrijk Bridge (Belgium) were protected by Abcite® X60. Abcite® was the most competitive and effective long term solution compared to the originally specified liquid paint alternative with 4 layers!

3 A rejuvenating cure for your assets

In 2011, these old and highly corroded benches started a new life with Abcite®.

4 Maintenance free corrosion protection for outdoor devices in extreme environments

Abcite® X60, the high performance and maintenance free anti-corrosion protection was selected by Göteborg Energi to protect cable cabinets delivered by ABB Kabeldon. The cabinets must withstand salt-laden air of the waterfront, rain, wind, snow clearance, temperature fluctuations, vandalism, etc. A reliable corrosion protection was consequently a major criteria for the good maintenance of the system.



Axalta Polymer Powders Switzerland Sarl

25 rue Saint Joseph

CH-1630 Bulle

Tel: +41 26 913 09 10


Fax: +41 26 913 01 99

Abcrite-info@axaltacs.com


Your local contact can be found at:

www.polymerpowders.axaltacs.com

Your Abcrite® partner

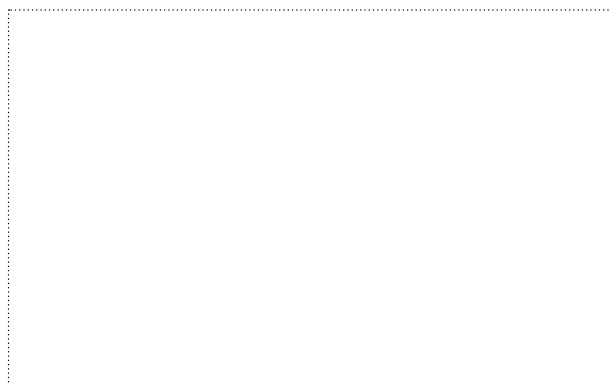

Abcite[®] Glassware

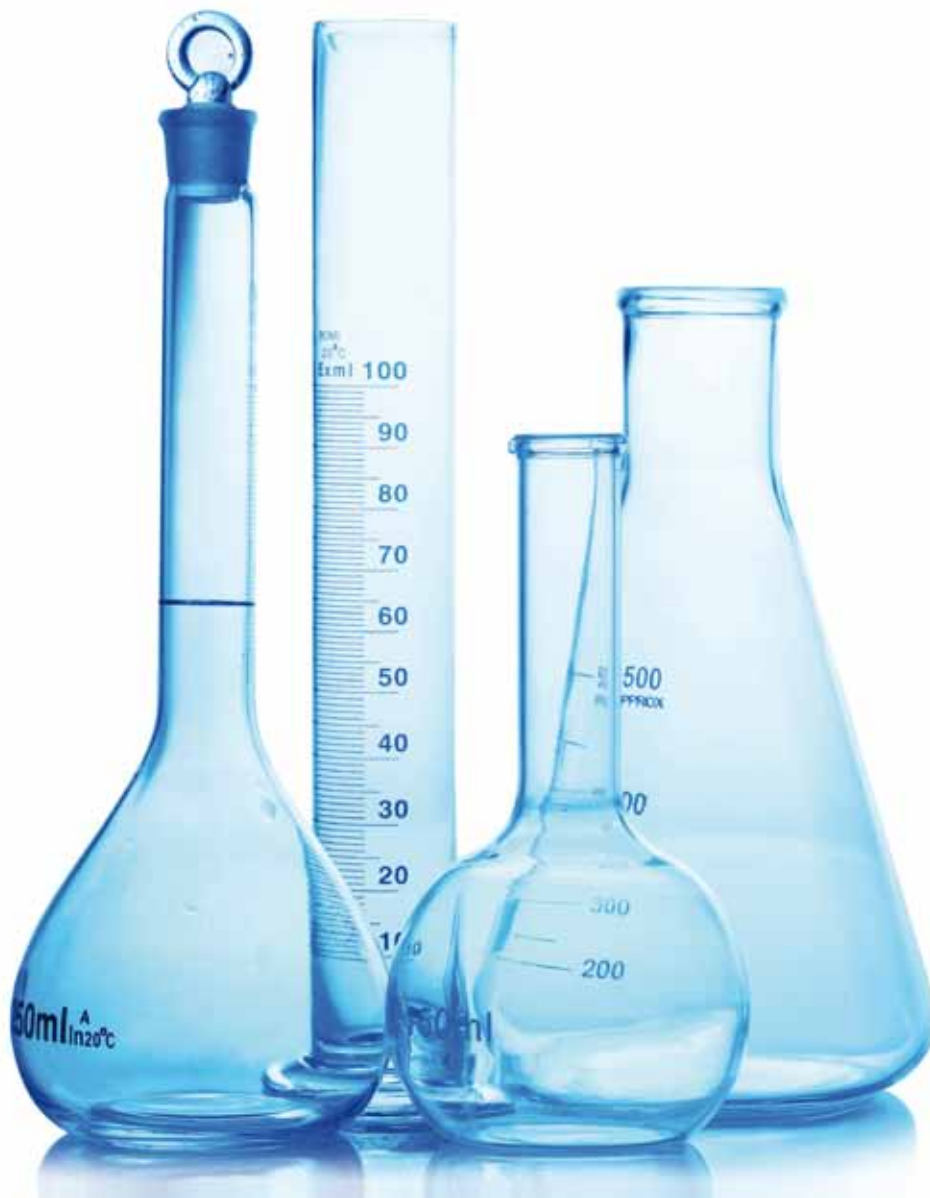

Glass made safe thanks to Abcite®

Shattering protection for glass surfaces

Glassware is frequently used for functional or decorative purposes. Glass is offering multiple advantages, but it has a main weakness, it can break.

Abcite® brings safety and the protection to all types of glassware.

Product features

- Superior adhesion on glass substrate
- Improves impact resistance
- Puncture and cut resistant
- High transparency
- High gloss
- Excellent chemical resistance (pH 1 to 12)
- Service temperature from -60 °C to 75 °C (should not be used for steam sterilizers)
- Environmentally friendly (no VOC, halogen free, BPA free)
- Easy to apply: by spraying or dipping
- Food contact compliant

Benefits

- Protection for functional or decorative glass: due to its high transparency, the product preserves the original glass appearance.
- Tough and strongly adhesive to glass, greatly improving the mechanical resistance of fragile glass pieces.
- In case of glass breakage, Abcite® protects users from injuries and prevents any exposure to the content of a glass container.



Typical applications

- Abcite® 585 EF is widely used as a shatterproof coating for glass bottles containing hazardous and expensive chemicals.
- It is well suited for coating light tubes intended for the food industry or medical facilities, where no glass splinters can be tolerated.
- For particularly fragile decorative glass or laboratory glassware, Abcite® 585 EF extends the pieces lifetime and enables a safe use.



Without Abcite®



With Abcite®



Simone Cenedese,
Master glassmaker,
Murano

Voice of the customer

Murano glass on board Fincantieri cruise ships: lighting and decoration made safe thanks to Abcite®.

Its refinement and precision cuttings have made Murano glass world famous. "Considered a luxury material, it is highly sought after as decoration for cruise ships", affirms Simone Cenedese, Master glassmaker in Murano worked closely with Axalta to bring this project alive. However Murano Glass drawbacks are its fragility and fragmentation when it breaks, with the potential of thousands of glass pieces harming passengers. Coating lightings made of Murano glass with Abcite® allows to avoid such fragmentation: while offering total transparency, Abcite® sticks extremely well to glass, containing pieces in case of breakage, thus preventing passengers from being injured.



Axalta Polymer Powders Switzerland Sarl

25 rue Saint Joseph

CH-1630 Bulle

Tel: +41 26 913 09 10


Fax: +41 26 913 01 99

Abcite-info@axaltacs.com

Your local contact can be found at:

www.polymerpowders.axaltacs.com

Your Abcite® partner

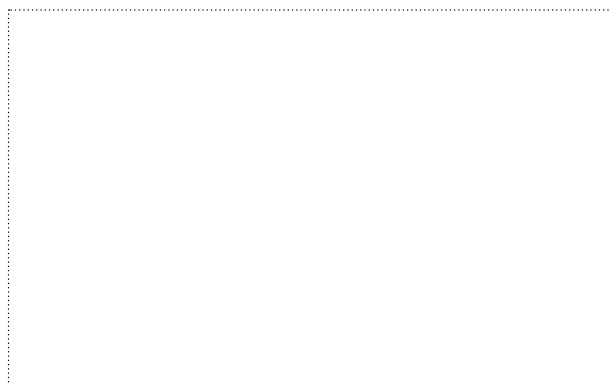

Abcite[®] Transportation



A tough coating for a demanding market

The automotive and transportation market is well known for its highest standards and specifications: safety and long-lasting performance are key. Thanks to its exceptional properties, Abcite® fits particularly well to this very demanding market.

Simple and robust

- Superior corrosion resistance:
 - C5-M and Im3 High according to ISO 12944-6
 - tested with very good results according to Volvo Indoor Corrosion Test STD 1027, 1375 (VICT)
- High impact and abrasion resistance: Abcite® passes most aggressive stone chip resistance tests (ISO 20567-1 "VDA-Test", Renault D24 1702, Ford BI 157-06, SAE J400)
- UV stability
- Excellent chemical resistance (pH 1 to 12)
- High adhesion and flexibility
- One-coat process: no primer required
- Strong electrical insulator
- Noise dampening properties
- Environmentally friendly (no VOC, halogen free, BPA free)
- Good edge coverage
- Can be overcoated by Alesta® powder coatings for decorative purposes

Benefits



- Maintenance free over the entire product lifetime
- Resistant over the years even under toughest climate conditions
- Time saving with better performances: can replace a 3-5 layers coating systems
- Color stability over the time
- No cracking on flexible parts

Typical applications

- Automotive Accessories:
 - Bike racks
 - Pipe fuel tanks
 - Battery casings
 - Door hangs
- Chassis
- Springs
- All other parts exposed to stone impacts



Product features

Abcite® 1060 / Abcite® X60		
Film thickness	Min. 300 µm	
External application - weathering resistance	Yes	
Service temperature	From -60 °C to 75 °C	
Application method - on preheated surface	Spraying Abcite® X60	Fluidized bed Abcite® 1060
		
Overcoating with decorative powder possible	Yes	
Stone chip resistances tests	Renault D24 1702: rating 5 at -30 °C; +23 °C; +80 °C	
	SAE J400: rating 4,5 - 5 at -30 °C; +23 °C	
Colors	Blue RAL 5012 and RAL 5017 Green RAL 6005 Grey RAL 7001 and RAL 7016 Black RAL 9005 White RAL 9016*	

*Other colors upon request



Proven performance: repair damaged nylon with Abcite®

Hundreds of US Marines LAV (Light Armored Vehicles) drive shafts used to be scrapped each year because of corrosion, as a result of the Nylon 11 coating disbonding from the metal, allowing moisture to penetrate under the coating. These damaged drive shafts are now being refurbished using Abcite®, which saves the Marines \$1.5 million each year. The flame-spray remanufacturing process was developed at the Rochester Institute of Technology and full testing showed that the corrosion protection and abrasion resistance in wet sand of Abcite® is equal or superior to the resistance of Nylon 11. Protected by Abcite®, these refurbished drive shafts can go back in service and withstand the extremely demanding operating conditions combining sea water and humidity, temperature variations, severe gravelling and sand abrasion, without being affected by corrosion.



Axalta Polymer Powders Switzerland Sarl

25 rue Saint Joseph

CH-1630 Bulle

Tel: +41 26 913 09 10


Fax: +41 26 913 01 99

Abcrite-info@axaltacs.com

Your local contact can be found at:

www.polymerpowders.axaltacs.com

Your Abcrite® partner

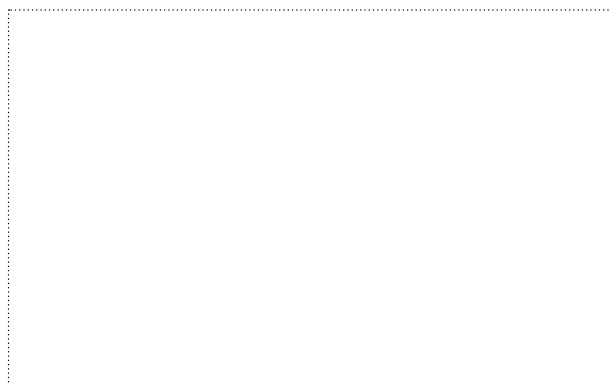

Get in Touch

For United Kingdom and Overseas:

Plascoat Systems Ltd
Farnham Trading Estate,
Farnham Surrey, GU9 9NY,
United Kingdom
Tel: +44 (0) 1252 733777
Email: Plascoat-salesUK@axalta.com

For Europe:

Plascoat Europe B.V.
PO Box 9,
3214ZG Zuidland
the Netherlands
Tel: +31 (0) 181 458 888
Email: Plascoat-salesNL@axalta.com

Or contact your local Axalta office

Your Plascoat® PPA 571 Partner:



AN AXALTA COATING SYSTEMS COMPANY



AXALTA COATING SYSTEMS



Plascoat® PPA 571

Proven Performance for Exterior Application

Pictures: © Shutterstock: Lmora wide | Deloyd Huenink | Vitali Aulasenka | Foo Ttoo | VDB Photos | Nor Gal |
Balonddi | maxuser | Kristina Postnikova | Pix One | SnapshotPhotos | Ant | Clausen Ventura
iStock: rafalkrakov | veslivo | Dreamstime: Iernamika

Nearly 30 Years of Proven Performance

Axalta's Plascoat® PPA 571 is a thermoplastic powder technology designed to provide long-term corrosion protection for metal against the most demanding environments.

A durable coating that has the versatility to work in a wide array of application and processing techniques including electro-static spraying flock spraying and fluid bed dipping.

Whatever the application Plascoat® PPA 571 has almost 3 decades of proven performance to back its credentials.

30
YEARS

Key Features

- Superior resistance to salt, sea, sand and sun
- Excellent abrasion protection
- High flexibility
- Excellent environmental credentials: no bisphenol A (BPA free), no VOCs, no TGIC, no phthalates, no isocyanates, no halogens and no heavy metals
- Sound insulation
- Electrical insulation
- Excellent coverage of edges and welds
- Very low smoke in event of fire

Benefits

- Highly durable: how extreme weatherability might be, Plascoat® PPA 571 provides long life for the coated assets
- Highly economical: no primer required, no maintenance during the product life
- Safe and dependable: easy to clean surface with a warm-touch effect
- Tough and resistance Plascoat® PPA 571 is unaffected by salt spray, stone chips and temperature extremes
- Universal and versatile
- Relies on almost 30 years proven performance

Used in a wide array of application

Fencing



Fencing

In this environment, resistance to high UV, intense heat, salt, sea and desert storms is key. Traditional coatings in these conditions do not last well, as many long-term fields test have shown. Plascoat® PPA 571 is used all over the world for chain link, ornamental and security fencing and meets all the requirement of ASTM F1043-08 and F668-07.

Key Benefits

- Superior resistance to salt, sea, sand and sun
- Excellent abrasion protection
- Excellent coverage of edges and welds

Proven Performance

Thousands of kilometres of fencing in the harsh climates of the USA, the Middle East and Australia have been successfully coated with Plascoat® PPA 571.

Live tests in the US have shown that the salt spray corrosion rate of Plascoat® PPA 571 are half those of standard powder coatings and the fading rate is 1/20th.



Outdoor furniture


Playground, street furnitures or lighting columns: all those objects are exposed to demanding climatic conditions, continual use or extreme corrosive attacks from urban environment.

Key Benefits

- Superior resistance to salt, sea, sand and sun
- Excellent abrasion protection
- Excellent environmental credentials: no bisphenol A (BPA free), no VOCs, no TGIC, no phthalates, no isocyanates, no halogenes and no heavy metals
- Easy to clean surface: due to its smooth surface graffiti can be easily wiped clean
- Provide grip and warm-to-the-touch feel

Proven Performance

Trials at the Swedish Corrosion Institute have proved that Plascoat® PPA 571 is one of only three out of 52 corrosion protection systems that can extend the life of a lighting column by up to 50 years.

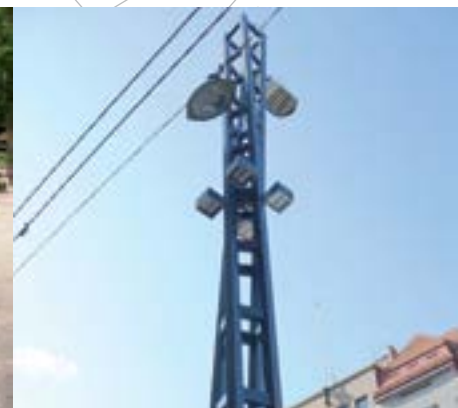

Outdoor Furniture

Construction Automotive



Construction

It is essential that steel and aluminium structures are protected from corrosion for as long as possible. Plascoat® PPA 571 is ideally suited to achieve this objective. Typical use include the coating of rock pins, the steel in reinforcement concrete and structure metalwork on bridges.

Key Benefits

- Highly durable: how extreme weatherability might be, Plascoat® PPA 571 provides long life for the coated assets
- Excellent environmental credentials: no bisphenol A (BPA free), no VOCs, no TGIC, no phthalates, no isocyanates, no halogenes and no heavy metals
- Highly economical: no maintenance during the product life
- Very low smoke in event of fire: the perfect coating solution in tunnels and enclosed public coatings

Proven Performance

Axalta relies on worldwide references of bridges or construction for the last 20 years, still in place, exposed to weather conditions and not requiring any maintenance.

Automotive

The automotive and transportation market is well known for its highest standards and specifications: safety and long-lasting performance are key. Plascoat® PPA 571 is popular because it is tough, flexible and stone chip resistant. Plascoat® PPA 571 is ideal to protect all kind of automotive accessories: bike racks, pipe fuel tanks, battery casings, door hangs, chassis, springs or all other parts exposed to stone impacts.

Key Benefits

- High durability through superior resistance to road salt and all climatic conditions
- Resistance over the years thanks to a very high impact and stone chip resistance
- Noise dampening properties
- Security, as the material is a strong electrical insulator
- Color stability over the time
- No cracking on flexible parts

Proven Performance

Plascoat® PPA 571 passed the stone chip resistance test SAE J400.



A Wider World of Applications

Furthermore Plascoat® PPA 571 will be used in a wide variety of applications, including fire extinguishers, battery boxes, fan-guards, tanks, school furniture, shopping trolleys, stadium seating and submersibles. Whatever the application, Plascoat® PPA 571 has long-term field tests to back its credentials





Plascoat® PPA 571

lasts and lasts and lasts ...



Product features and performance

Corrosion Resistance	More than 20 000 hours salt spray testing according to ASTM B117, with no blistering, cracking, corrosion or flaking	
	1000 hours salt spray testing according to ASTM B117 with an under-film corrosion between 0 and 0,5 mm from scribe (on pre-treated steel)	
	Zero loss of adhesion when tested to ASTM D3359-A	
UV Stability	No significant change in colour, gloss or mechanical properties: after 2000 Hours QUV ASTM G154-06, Xenon arc or Five years in Florida at 45 °C to the sun by the sea	
Mechanical Resistance	Over half of Plascoat® PPA 571 coating still remained after one million cycle of tumbling (salt and grit) according to ASTM A 926-94 whereas all other coatings tested (including thermosets and galvanising) were completely stripped	
	Passed stone chip resistance Test according to SAE J400	
Chemical Resistance	Excellent chemical resistance. Meets Water industry standards (WIS 4 52 01 or AS/NZS 4158) and will protect metal from aggregate slurries.	
Electrical Insulation	Good electrical insulation properties Volume resistivity: 3 x 10 ¹⁷ ohm.cm. (measured on black) in accordance with standard IEC 93	
	Electric resistance, coupled with its high dielectric strength: 47.8 KV/mm (measured on white, IEC 243) when measured at 370 microns	
Approvals	Food contact and drinking water approvals available for specific grades. Only upon request.	
Fire Properties	Very low toxicity of the fumes: Toxicity index of 1.78 (NES 713), whilst Royal (British) Navy requirement is 5 max. Toxicity index of 0.21 (BS 6853:1999) used for London Underground Projects	
	Very low density of the fumes generated: Index of 1.13 (A0 (ON)) (BS 6853:1999) used for London Underground Projects with a requirement f 2.6	
	Class 0 according to BS 476	
Surface Properties	Plascoat® PPA 571 contains no reactive ingredients and provides little “anchor” or food for seaweed, barnacles and lichen. While not specifically anti-fouling, the rate of growth of algae, fungus, mildew and marine flora or faune is slower than many other coatings	
Graffiti Removal	Many metro, subway and city authorities around the world including the Paris Metro and Stockholm City have confirmed that graffiti and fly-poster adhesives can be easily removed from Plascoat® PPA 571. Plascoat® PPA 571 is impermeable to graffiti paints. Therefore, often you can wipe the graffiti off with just a cloth (but a small amount of solvent on the cloth will help). Standard water-based graffiti removal products remove the graffiti paint within just a few wipes.	
Application Method		
	Electrostatic or Flock Spray with Plascoat® PPA 571ES	Fluidised Bed with Plascoat® PPA 571
Pre-Treatment	Plascoat® PPA 571 will survive many years outside in adverse environments if undamaged. However, should damage through to the metal occur at any stage it is necessary that the pre-treatment allows the coating to continue to adhere to the metal for as long as possible. All metal items should therefore be clean, degreased and free from rust. Plascoat® recommend the use of grit-blasting at least to Sa 2,5 (Swedish Standard) for dip coating or the use of Zinc Phosphate systems for spray coating. Certain chromates (if compliant with local authority legislation) and resin-based systems can also be used. If iron phosphate is used, Plascoat® recommend the use of suitable rinse. We have found exceptional results with certain silane-based rinses and pre-treatments.	
Overcoating	Given the correct procedures, Plascoat® PPA 571 can be over-sprayed with Alesta Polyester Powder Coatings to provide an almost infinite variety of colours and finishes.	

The information provided herein corresponds to our knowledge on the subject at the date of its publication. This information may be subject to revision as new knowledge and experience becomes available. The data provided fall within the normal range of product properties and relate only to the specific material designated; these data may not be valid for such material used in combination with any other materials or additives or in any process, unless expressly indicated otherwise. The data provided should not be used to establish specification limits or used alone as the basis of design; they are not intended to substitute for any testing you may need to conduct to determine for yourself the suitability of a specific material for your particular purposes. Since Plascoat cannot anticipate all variations in actual end-use conditions Plascoat makes no warranties and assumes no liability in connection with any of this information. Nothing in this publication is to be considered as a license to operate under or a recommendation to infringe any patent rights.

Success Stories

Fencing at sea side in Australia



In 1996 a local Brisbane coating company recommended Plascoat® PPA 571 in a tender to remove, sand blast, re-coat and re-install fences in Sutton Beach, one of Brisbane's seaside parks. Whilst it took only 6 months for the previous chosen coating technology to corrode completely, fences coated with Plascoat® PPA 571 still look like new today.



Gas pipeline security fence in the UAE



The climate in the United Arab Emirates is very demanding on coated metal. Sacrificial zinc, polyester and PVC coatings can be quickly stripped off the metal by wind-blown sand. Very high levels of UV can also cause coatings to degrade and fail after just a few years. Due to its outstanding performance on corrosion resistance, UV stability and abrasion resistance, Plascoat® PPA 571 has been chosen to do the job. Since 2001 the fence is still in place without any damages.

Success Stories

Unique product for unique projects

The tale of 2 coatings in Indiana, USA



2011 Plascoat® PPA 571 was chosen to recoat Lighting columns, crash barriers, railings and public information board on the Jackson Street Bridge in Indiana. A mile down the road standard polyester coatings has been applied on similar furniture for comparison. After 2 harsh winters, the polyester coatings already began to flake off while Plascoat® PPA 571 still looked new.



It is essential that steel and aluminium in construction projects are resistant to corrosion for many years without costly maintenance programmes.

Pictures with courtesy of Cox Architecture

2011 Plascoat® PPA 571 had again the opportunity to demonstrate its performance by an Australian famous architectural project, the Kulripa Bridge in Brisbane. This award-winning masterwork was designed as pedestrian bridge over the Brisbane river using a unique tensile structure combining multiple masts and cable trays which gives this bridge the silhouette of a ship cruising the river.

Plascoat® PPA 571 has been chosen to protect the handrail support structure from corrosion and withstand the tough Australian climate and environment of a pedestrian bridge crossed by hundreds of people per day.

Bridge structure under spanish climate

1990 Plascoat® PPA 571 has been chosen to protect steel and aluminium tubular parts of a footbridge in northern Spain (San Sebastian), as existing Polyamide coating started to peel off already after few months. The search was on for a coating that could accommodate the wide temperature range, provide a high level of UV resistance, resist to vandalism, meet the requirements of a tightening budget, and offer a coating life in excess of 10 years. Whilst other part needed to be recoated several time, Plascoat® PPA 571 is still in place since 1990, with no trace of under film corrosion or blistering.



No under-film corrosion after years of exposure.

Success Stories

700 lamp posts in Finland



Pictures courtesy of FSP Finnish Steel Painting Oy

The fast-growing city of Tampere, located on a narrow isthmus between 2 great lakes in the south of Finland started a new public transportation project, in order to relieve the city center from traffic whilst improving the environmental impact. The project involves 2 tramlines crossing the city center and consequently the installation of posts along the route, assuring lighting and supporting overhead lines.

3 different designs of posts have been chosen, from decorative one's to multifunctional in ladder shape, all coated with Plascoat® PPA 571.



On Aruba, a large part of the power supply is supplied by solar panels at the airport.

For this large-scale solar energy project, a Dutch coater powder coated the steel structure. The roof has an area of 24,000 m² and is equipped with 14,000 solar panels that produce approximately 7,000,000 kWh on an annual basis.

The biggest challenge with this project was the Caribbean maritime climate on Aruba. The circumstances demanded a coating system that could withstand the high salinity in the air to prevent corrosion. Combining different expertise enabled the Dutch coater to develop a completely new coating system using Plascoat® PPA 571. This system still manages to guarantee the required high quality under severe conditions.

Colourful Performance

Broad choice of colours

Plascoat® PPA 571 is available in these listed stock colours. A comprehensive colour matching service is available for larger orders. Please contact us for further details. Our colour range is listed in 3-digit codes and RAL 4-digit identification numbers where appropriate.



Beige 222 RAL 1015



Yellow 344 RAL 1021



Blue 536 closest RAL 5017



Grey 613 RAL 7035



Grey 695 closest RAL 7046



Brown 813 RAL 3009



Black 700 RAL 9005



Silver RAL 9006



Red 233 RAL 3020



Green 475 RAL 6005



Blue 542 RAL 5015



Grey 654 RAL 7001



Grey 640 RAL 7016



Brown 838 closest RAL 8019



White 110 RAL 9016

Please note: whilst every effort is made to ensure the colours on this page are as accurate as possible, due to printing and on-screen limitations, these colours should be used as guidance only. Colours reflect coated finish, and matched to nearest RAL number where appropriate. Samples are available as coated plates or powder.



A PROVEN LEGACY, AN EXCITING FUTURE

Rilsan[®] polyamide 11



INTRODUCTION

Developed by Arkema more than 70 years ago, Rilsan® PA11 is a high performance reference in the world engineering polymers.

Produced from a renewable source (castor oil), Rilsan® PA11 is used in a large number of applications thanks to its outstanding properties, including excellent chemical resistance, easy processing, high and low temperature performance (-40°C / +130°C), high dimensional stability, and low density. Many industries around the world (e.g. automotive, textile, oil & gas, wire & cables, electronics) have used Rilsan® PA11 for many decades for its long-term durability.

Rilsan® PA11 is easy to process using most processing technologies (extrusion, extrusion-blow molding, injection molding, rotomolding, and 3D printing).

The PA11 matrix accommodates countless additives and filling agents, such as plasticizers, stabilizers, colorants, lubricants, impact modifiers, glass fiber, carbon fiber, etc. A variety of grades are available, packaged in sealed bags or containers ready for use. Rilsan® PA11 is produced in Europe, North America, and Asia.

CONTENTS

3 APPLICATIONS

4 NOMENCLATURE

5 MATERIAL PROPERTIES

Physical Properties

Thermo-Mechanical Properties

Mechanical Properties

Long-Term Performance

Chemical Resistance

Permeability

16 PROCESSING

Rheological Properties of Rilsan® PA 11

Preparation of Rilsan® PA11

Processing of Rilsan® PA11

APPLICATIONS

AUTOMOTIVE

- Specific Properties:
 - Cold impact resistance
 - Ageing resistance
 - Resistance to hydrocarbons
 - Resistance to zinc chloride
 - Flexibility
- Applications:
 - Fuel lines
 - Fluid transfer lines (brake, clutch, cooling)
 - Quick connectors, fittings, fasteners and clips
 - Friction parts



INDUSTRIAL VEHICLES

- Specific Properties:
 - Cold impact resistance
 - Chemical resistance
 - Flexibility
 - Ageing resistance
- Applications:
 - Air brake tubing for trucks
 - Hydraulic hoses
 - Fuel lines, clutch lines
 - Quick connectors, fittings, fasteners and clips



PNEUMATICS

- Specific Properties:
 - Flexibility
 - Chemical resistance
 - Burst strength
- Applications:
 - Pneumatic hoses, air lines
 - Hydraulic hoses



AEROSPACE

- Specific Properties:
 - High and low temperature performance
 - Dimensional stability
 - Resistance to fuel
- Applications:
 - Electrical cable sheathing
 - Hydraulic hoses
 - Oil tanks
 - Air-conditioning hoses and ducts



ELECTRICAL & ELECTRONICS

- Specific Properties:
 - Chemical resistance
 - Easy processing
 - Smooth surface finish
 - Resistance to termites
 - Abrasion resistance
- Applications:
 - Optical cable sheathing
 - Copper cable sheathing
 - Connectors
 - Housings
 - Fasteners, clips, and mechanical parts



OIL & GAS

- Specific Properties:
 - Resistance to hydrocarbons
 - Ageing resistance
 - Flexibility
 - Easy processing
- Applications:
 - Umbilical lines and hoses
 - Gas pipes and fittings (t-fittings, valves, reducers)
 - Flexibles (flow-lines, risers)
 - Flexible liners for offshore and on-shore applications
 - Cables



MEDICAL & FOOD PACKAGING

- Specific Properties:
 - Food and medical compliant grades (Europe, FDA, USP Class VI)
 - Chemical resistance
 - Low gas permeation (O_2 , CO_2)
- Applications:
 - Nutrient and solution bags
 - Masks, hearing aides
 - Food casing
 - Beverage tubing



SPORTS

- Specific Properties:
 - Lightweight
 - Energy return
 - Fatigue resistance
 - Abrasion and scratch resistance
 - Cold impact resistance
- Applications:
 - Racket eyelets and bumpers
 - Badminton shuttlecocks
 - Ski top layers
 - Shoe midsole and outsoles
 - Textiles



TEXTILES & MONOFILAMENTS

- Specific Properties:
 - Chemical resistance
 - Dimensional stability
 - Abrasion resistance
 - Flex fatigue resistance
 - Easy extrusion
- Applications:
 - Technical and high-end fabrics
 - Brushes
 - Industrial woven fabrics
 - Filters



NOMENCLATURE

Standard Rigid and Plasticized Grades:

B	ES	N	BLACK	P	40	TL
POLYAMIDE TYPE B = PA11	PROCESSING EC = Cable Sheathing ES = Extrusion or Blow Molding M = Injection Molding	VISCOSITY F = Fluid N = Normal V = Viscous HV = High Viscosity	COLOR O = Natural Black Color + Reference	RATE OF FLEXIBILITY P1 TO P6 = Flexibility Index	REFERENCE NUMBER	STABILIZERS AND OTHER ADDITIVES PTL, T6L, T8L = Heat - Light Stabilizers W = Flame Retardant G, Y = Self Lubricating D = Mold Release Agent A = Food Contact Approved NL = No Lubrication NB = Non-glossy C = Conductive CC = Transparent

Standard Reinforced Molding Grades:

B	ZM30	BLACK	TL
POLYAMIDE TYPE B = PA11	TRANSFORMATION Z = Glass Fiber S = Carbon Fiber M = Injection Molding # = Filler Amount	COLOR O = Natural Black Color + Reference	STABILIZERS AND OTHER ADDITIVES TL = Heat - Light Stabilizers W = Flame Retardant G, Y = Self Lubricating D = Mold Release Agent A = Food Contact Approved NL = No Lubrication NB = Non-glossy C = Conductive CC = Transparent

A few examples of Rilsan® PA11 grades designations:

RIGID	BMNO TLD; BESNO TL; BESVO A FDA
SEMI-RIGID	BESNO P20 TL
FLEXIBLE	BESNO P40 TL
REINFORCED	BZM30 Black TL

Special grades can be developed to fulfill specific customer requirements.




MATERIAL PROPERTIES

PHYSICAL PROPERTIES

Density

Compared to other high performance polymers, Rilsan® PA11 offers very low density, up to 6 times lighter than metal. This is a significant economic advantage when studying the cost versus performance aspect of using Rilsan® PA11.


Comparative Densities of Engineering Polymers & Aluminum (g/cm³)

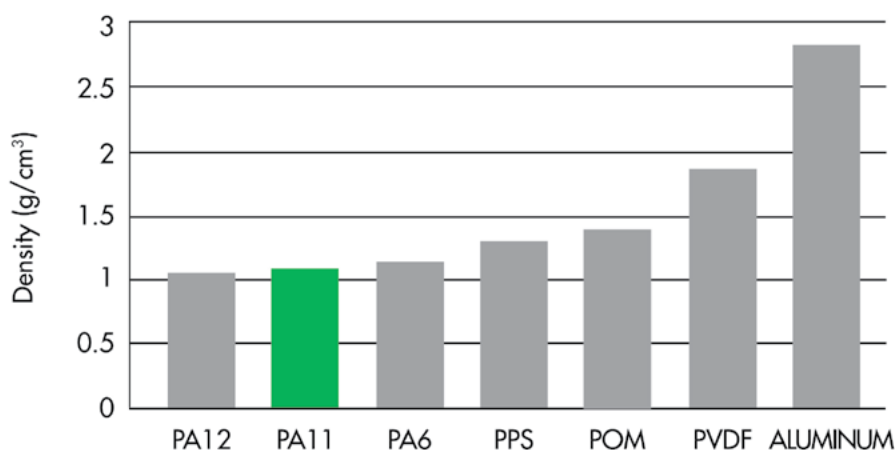

Moisture pick-up


Among all performance polyamides, Rilsan® PA11 has very low moisture pick-up. Other polyamides feature a more hydrophilic behavior resulting from the polarity of the amide group in the backbone. Due to its low concentration of amide groups, Rilsan® PA11 can be used in a wide range of humidity environments. The absorption characteristics of Rilsan® PA11 are similar when it is exposed to other polar liquids such as alcohols, acids and esters. This low moisture pick-up results in outstanding dimensional stability of final parts made with Rilsan® PA11.

Water absorption based on relative moisture rate of Rilsan® PA11 and PA12 vs various polyamides, as per ISO 62 standard

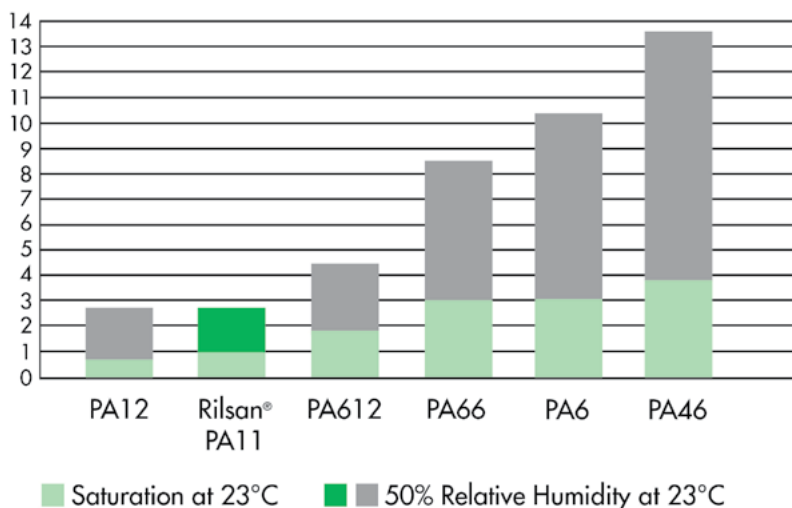

The following table shows the dimensional stability of Rilsan® PA11 and PA6 after 25 weeks of immersion in water at 20°C.

	LENGTH VARIATION	WEIGHT VARIATION
RILSAN® PA11	0.2 - 0.5%	1.9%
PA6	2.2 - 2.7%	9.5%

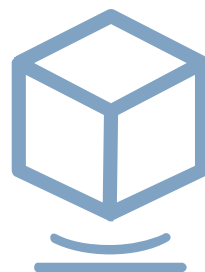



THERMO-MECHANICAL PROPERTIES

Phase Transition

Rilsan® PA11 is a semi-crystalline thermoplastic polymer featuring 2 phase transitions:

- Melting range between 180°C and 189°C (depending on the grade), which corresponds to fusion of the crystalline phase. It occurs 10°C higher than PA12, due to a greater density of hydrogen bonds.
- A glass transition temperature (T_g) at about 45°C, corresponding to transition of the amorphous phase, approximately 5°C higher than PA12.

The following table provides the melting ranges of several Rilsan® PA11 and Rilsamid® PA12 grades, per the ISO 11357 standard.

	UNIT	STANDARD MOLDING GRADES		STANDARD EXTRUSION FLEXIBLE GRADES	
		AMNO TLD (PA12)	BMNO TLD	AESNO P40 TL (PA12)	BESNO PA40 TL
MELTING RANGE	°C	178	189	171	182

Thermal Stability

Rilsan® PA11 offers greater thermal stability than PA12 and can be used continuously at 125°C under certain conditions. Additionally, it can withstand intermittent peaks of up to 150°C. For higher temperatures ask our team about the Rilsan® HT range.

It can also withstand cold temperatures, and maintains its high impact resistance at -40°C. For extreme climate conditions, a special grade is available that can withstand temperatures down to -60°C. Rilsan® PA11 is the only polyamide in the world capable of performing in such harsh environments.

The table below features the typical service temperatures for Rilsan® PA11 and Rilsamid® PA12 compared to PA6 and PA66.

	UNIT	RILSAN® PA11	RILSAMID® PA12	PA6	PA66
OPERATING TEMPERATURE	°C	100	90	100	110

The following table features the continuous service and temperature peaks for historical standard Rilsan® PA11 and Rilsamid® PA12 grades per a major car OEM standard for a 1,000-hour continuous test with temporary 16-hours temperature peaks.

	UNIT	RILSAN® PA11	RILSAMID® PA12
CONTINUOUS	°C	125	100
TEMPERATURE PEAKS	°C	150	125

* *Best-in-class extrusion PA11 grades can now withstand 170°C for 1000h. At similar composition, PA11 will exhibit 10-20°C greater performance than equivalent PA12 grades.





Heat Distortion Temperature Under Load

As a result of its inherent cohesion forces, Rilsan® PA11 exhibits high heat distortion temperatures under load, in excess of those of PA12. The values obtained show that at high temperatures, Rilsan® PA11 retains its mechanical properties and exhibits higher creep resistance than PA12.

The following table features the heat distortion temperature (HDT) under load for various Rilsan® PA11 and Rilsamid® PA12 grades, as per ISO 75 standard.


	UNIT	BMNO TLD	AMNO TLD (PA12)	BESNO PA40 TL	AESNO PA40 TL (PA12)	BZM30 OTL	AZM30 OTLD (PA12)
HDT UNDER 0.46 MPA	°C	145	130	130	125	180	175
HDT UNDER 1.85 MPA	°C	50	45	45	45	175	170

Vicat Temperature

Rilsan® PA11 boasts a higher vicat softening temperature than PA12. This temperature, which depends on molding conditions, varies significantly based on the flexural modulus of the grade.

The following table features the vicat points for Rilsan® PA11 vs Rilsamid® PA12, per the ISO 306 standard.

	UNIT	BMNO TYPE (PA11)	AMNO TYPE (PA12)
VICAT POINT UNDER 1 daN	°C	180	170
VICAT POINT UNDER 5 daN	°C	160	140

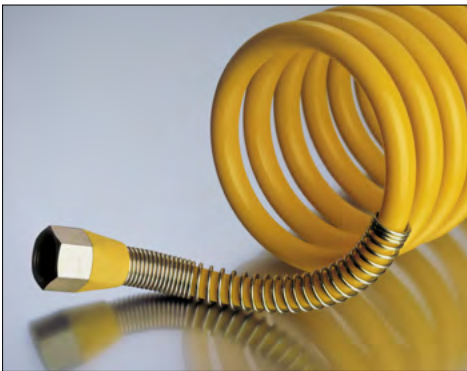





MECHANICAL PROPERTIES

Tensile Strength

Rilsan® PA11 exhibits excellent mechanical properties over a wide temperature range. It has high elongation at break and high tensile strength at break and at yield. It is one of the toughest high performance polymers and is therefore used extensively in demanding applications. At ambient temperature, the tensile strength of rigid (unmodified) PA12 leads to noticeable necking at around 20% elongation. In the same conditions, rigid Rilsan® PA11 first produces “diffuse necking”, up to 40% elongation, beyond which necking occurs. As shown by the graph below, Rilsan® PA11 provides a significant safety factor in mechanical stress over PA12.

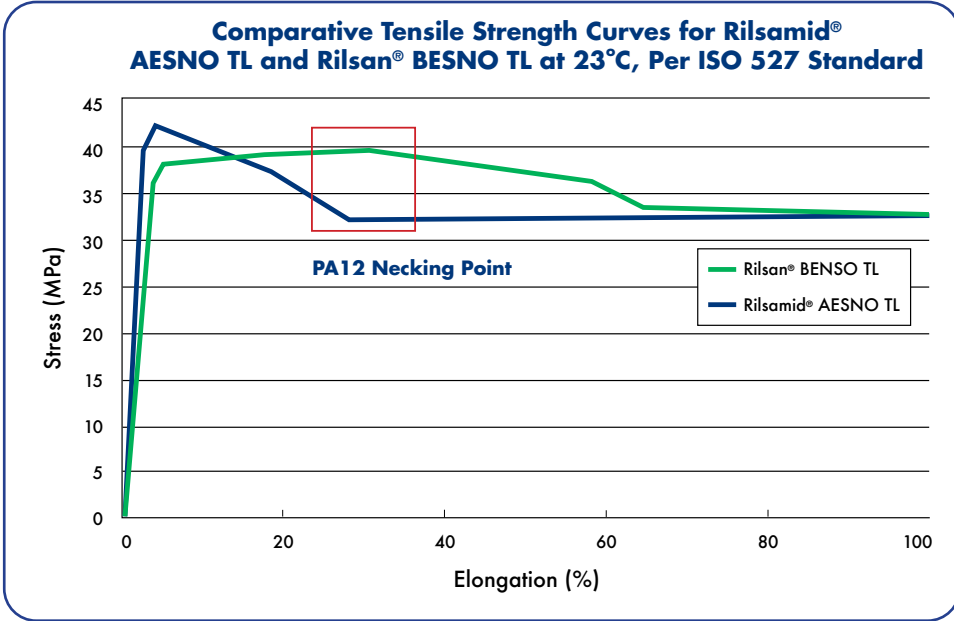


This very different performance can be attributed to the greater strength of the Rilsan® PA11 crystallites (triclinic/hexagonal) compared to the PA12 crystallites (monoclinic). This better stability of Rilsan® PA11 compared to PA12 observed above with rigid grades also applies to plasticized grades from 23°C to the melting point (the disparity increases with temperature). A significant consequence of this difference in behavior in actual use is that, at equivalent modulus, a Rilsan® PA11 plasticized tube exhibits a higher burst pressure than its PA12 counterpart.

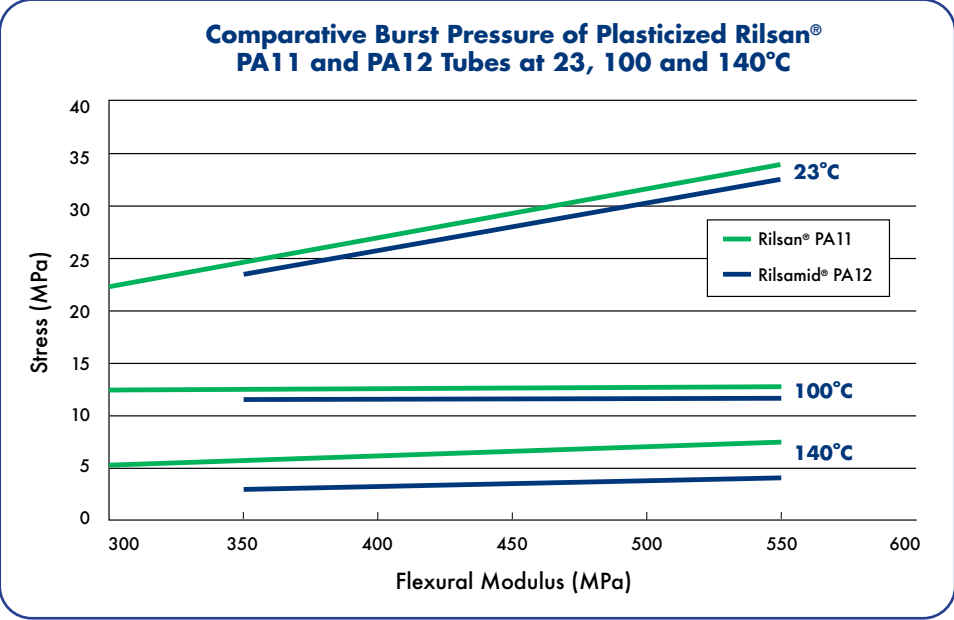



The increase in plasticizer content significantly changes the tensile behavior of Rilsan® PA11 grades as shown in the following graph below.

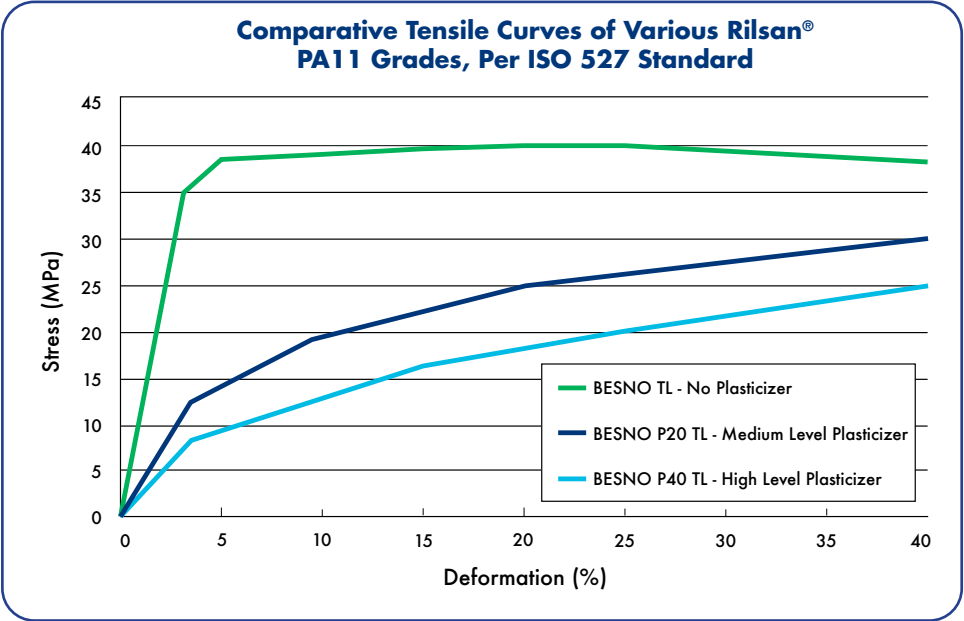

	YOUNG'S MODULUS AT 23°C DRY STATE (MPa)	STRESS AT YIELD (MPa)	ELONGATION AT YIELD (MPa)	TENSILE STRENGTH AT BREAK (MPa)	ELONGATION AT BREAK (%)
BESNO TL	1450	40	6	53	300
BESNO P20 TL	500	32	20	20	300
BESNO P40 TL	335	27	30	48	300

The influence of temperature on the tensile strength of Rilsan® PA11 is typical of the performance of thermoplastics.

The Young's modulus of BESNO P40 TL at various temperatures is detailed in the following table:

TEMPERATURE (°C)	23	60	80	100
YOUNG'S MODULUS (MPa)	335	173	166	160




Flexural Modulus

Rilsan® PA11 is available in a wide range of flexibilities. The modulus varies from 1200 MPa for non-plasticized grades to around 150 MPa for plasticized grades. Adding specific fillers (e.g. glass fiber, carbon fiber) enable an increase in modulus up to 8000 MPa. In dry conditions, PA6 and PA66 have significantly higher rigidity than Rilsan® PA11, but after moisture pick-up, the flexural properties of Rilsan® PA11 remain relatively stable.


Impact Resistance

Rilsan® PA11 demonstrates very good impact resistance at room temperature as well as at very low temperatures leading to a significantly higher safety factor than for PA12. In Charpy notched impact test at -30°C, Rilsan® PA11 is twice as resilient as PA12. Its fragile/ductile transition is ~35°C versus ~50°C for PA12. This benefit of Rilsan® PA11 applies to both unplasticized and plasticized grades. Glass transition temperatures are similar for Rilsan® PA11 and PA12 (a slight advantage of 5°C for Rilsan® PA11) and do not explain differences in performance between the products. This is due to the finer crystalline grid and spherulitical structure in Rilsan® PA11. Its impact resistance is also influenced by molecular weight and poly-dispersity. The impact resistance of Rilsan® PA11 at low temperature is twice that of PA12 (see graph to the right).

Effect of ambient conditions on the flexural modulus of Rilsan® PA11 and PA12 vs PA6 and PA66. Tests conducted per ISO 178 standard

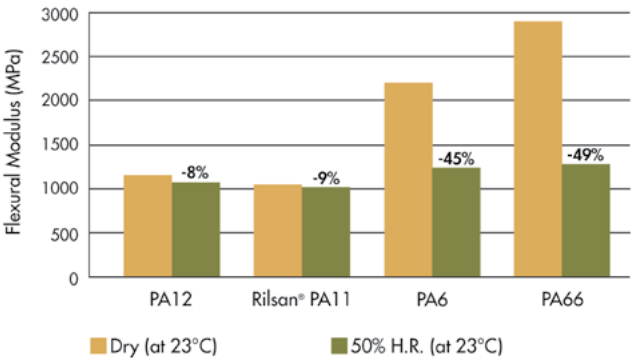

Comparative impact resistance of Charpy notched plasticized Rilsan® PA11 and PA12 (-30°C), per ISO 179/1eA standard

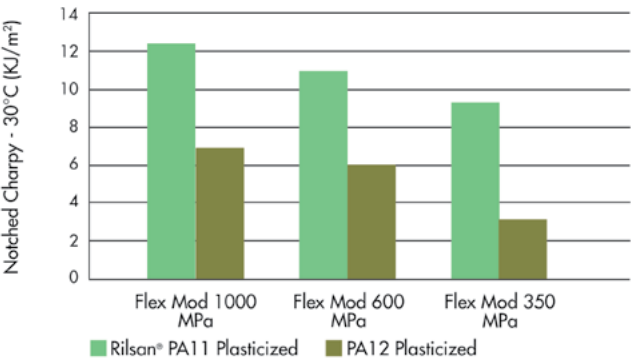


Comparative table of impact resistance of unnotched Charpy Rilsan® PA11 vs PA6, PA66 and PBT

	STANDARD	UNIT	RILSAN® PA11	PA6	PA66	PBT
UNNOTCHED AT +23°C	ISO 179/1eU	KJ.m²	No Break	75	50	300
UNNOTCHED AT -30°C	ISO 179/1eU	KJ.m²	No Break	40	40	300

Abrasion Resistance and Coefficient of Friction

Compared to other engineering polymers, Rilsan® PA11 features good abrasion resistance and crack propagation resistance. This is largely due to its smooth surface finish, that induces a low friction coefficient. Rilsan® PA11 also features greater abrasion resistance than PA12.

Comparative TABER (method CS17: 1000 revolutions under 1000 grams) abrasion resistance of Rilsamid® AESNO (PA12) and Rilsan® BESNO (PA11)

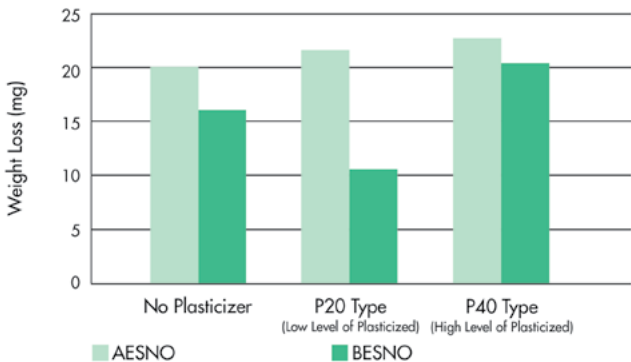




LONG-TERM PERFORMANCE

Creep Resistance


The notion of a material's lifetime is an important factor when designing components requiring long-term performance in specific operating conditions. As a general rule, Rilsan® PA11 features viscoelastic behavior at ambient temperature. However, under permanent stress, above a certain limit, Rilsan® PA11 undergoes plastic deformation. Arkema's material specialists have developed significant in-house expertise in predicting the long-term performance of parts made out of Rilsan® PA11. Our sales and development team will be pleased to provide further information.

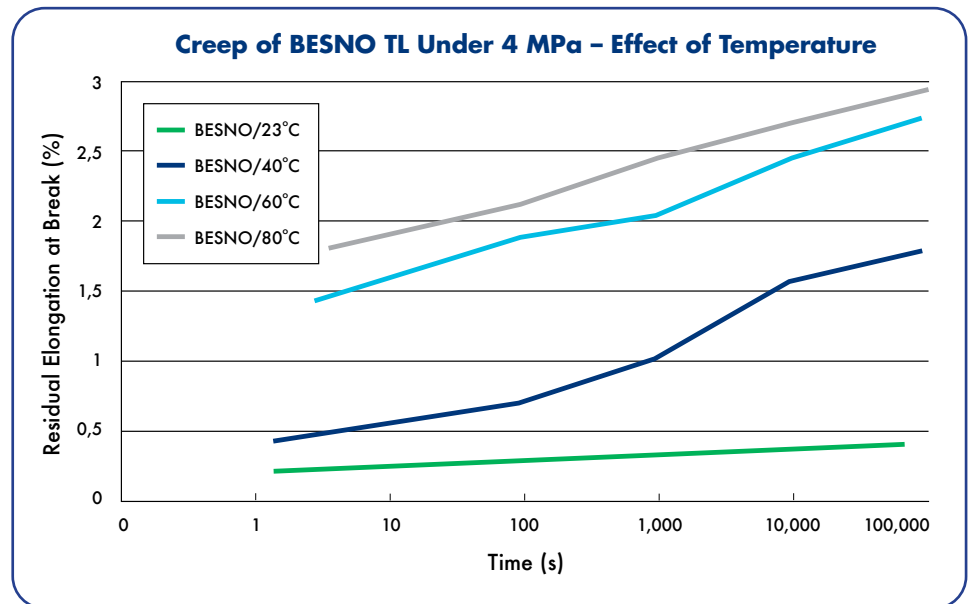

Weathering Resistance

Parts made with Rilsan® PA11 perform very well in a wide variety of climates around the world. Rilsan® PA11 is particularly resistant to degradation from the combined effect of the sun's rays and rainwater. The use of stabilizer packages also help to further increase the weathering resistance of natural and colored grades.

The following diagram shows the influence of the exposure site on the residual elongation at break of Rilsan® BESNO P40 TL.

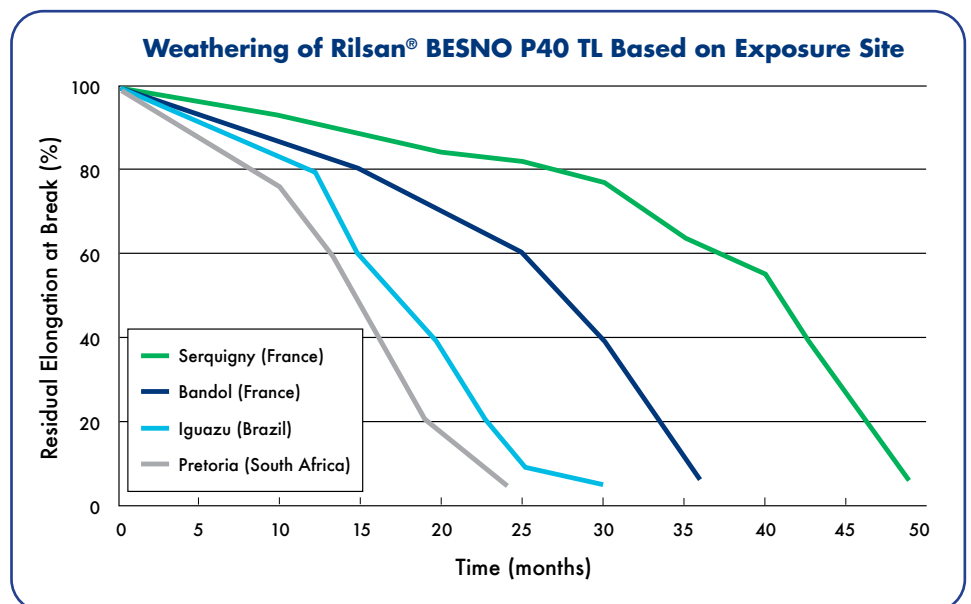

- **Serquigny, France:** temperate and humid climate, typical of Central Europe
- **Bandol, France:** hot and humid, typical Mediterranean climate
- **Iguazu, Brazil:** tropical climate
- **Pretoria, South Africa:** hot and dry climate





Chemical Resistance

Rilsan® PA11 offers a great balance between the resistance to grease and hydrocarbons and the resistance to acids, bases and salts. The excellent chemical resistance of Rilsan® PA11 is reflected both in high dimensional stability under harsh conditions and in the non-degradation of the polymer matrix. Additionally, Rilsan® PA11 features greater resistance to hydrocarbons than PA12, making it a preferred material for highly demanding applications in the oil and gas industry, such as offshore flow-lines.

Rilsan® PA11 features outstanding resistance to oils, hydraulic fluids, and fuels. Compared to polyester-based thermoplastic elastomers and other polyamides, Rilsan® PA11 offers a better combination of properties:

- Stability of strong mechanical properties
- Excellent dimensional stability due to a lower absorption rate (significant in the case of tubing carrying fluids, to minimize risk of leakage at the connection sites)

- Excellent inherent flexibility
- Very low permeability to hydrocarbons

The following tables feature the resistance of Rilsan® PA11 to common chemicals after 18-months of exposure.

- G** = Good
L = Limited (swelling – suitability depends on specific use and duration)
P = Poor
 * Slight Browning
 ** Swelling Action

CHEMICAL AGENT	CONCENTRATION (100%)	PERFORMANCE			
		20°C	40°C	60°C	90°C
MINERAL ACIDS					
Hydrochloric Acid	1%	G	L	P	P
	10%	G	L	P	P
Sulphuric Acid	1%	G	L	L	P
	10%	G	L	P	P
Phosphoric Acid	50%	G	L	P	P
Nitric Acid	Any Concentration	P	P	P	P
Chromic Acid	10%	P	P	P	P
Sulphur Dioxide		L	P	P	P
MINERAL SALTS					
Calcium Arsenate	Concentration or Boiled Solutions	G	G	G	
Soda Carbonate	"	G	G	L	P
Baryum Chloride	"	G	G	G	G
Potassium Nitrate	"	G*	L*	P	P
Di-ammonium Phosphate	"		G	G	L
Trisodic Phosphate	"	G	G	G	G
Alumina Sulphate	"	G	G	G	G
Ammonium Sulphate	"	G	G	L	
Copper Sulphate	"	G	G	G	G
Potassium Sulphate	"	G	G	G	G
Sodium Sulphide	"	G	L	L	
Calcium Chloride	"	G	G	G	G
Magnesium Chloride	50%	G	G	G	G
Sodium Chloride	Saturated	G	G	G	G
Zinc Chloride	Saturated	G	G	L	P

CHEMICAL AGENT	CONCENTRATION (100%)	PERFORMANCE			
		20°C	40°C	60°C	90°C
MINERAL BASES					
Soda		G	L	P	P
Potash	50%	G	L	P	P
Ammonia	50%	G	G	G	G
Ammonia Solution	Concentrated Liquid or Gas	G	G		
OTHER MINERAL BODIES					
Water		G	G	G	G
Sea Water		G	G	G	G
Carbonated Water		G	G	G	G
Bleach		L	P	P	P
Hydrogen Peroxide		G	L		
Oxygen	20 Volume	G	G	L	P
Hydrogen		G	G	G	G
Ozone		L	P	P	P
Sulphur		G	G		
Mercury		G	G	G	G
Fluorine		P	P	P	P
Chlorine		P	P	P	P
Bromine		P	P		
Agricultural Spray Solution			G	G	
Potassium Permanganate	5%	P	P		
ORGANIC BASES					
Aniline	Pure	L	P	P	P
Pyridine	Pure	L	P	P	P
Urea		G	G	L	L
Diethanolamine	20%	G	G**	G**	L

CHEMICAL AGENT	CONCENTRATION	PERFORMANCE			
	(100%)	20°C	40°C	60°C	90°C
ORGANIC ACIDS AND ANHYDRIDES					
Acetic Acid		L	P	P	P
Acetic Anhydride		L	P	P	P
Citric Acid		G	G	L	P
Formic Acid		G	P	P	P
Lactic Acid		G	G	G	L
Oleic Acid		G	G	G	L
Oxalic Acid		G	G	L	P
Picric Acid		L	P	P	P
Stearic Acid		G	G	G	L
Tartaric Acid	Saturated Solution	G	G	G	L
Uric Acid		G	G	G	L
HYDROCARBONS					
Methane		G	G	G	
Propane		G	G	G	
Butane		G	G	G	
Acetylene		G	G	G	
Benzene		G	G**	L	
Toluene		G	G**	L	L
Xylene		G	G**	L	L
Styrene		G	G**		
Cyclohexane		G	G	L	
Naphtalene		G	G	G	L
Decaline		G	G	G	L
FORANE® 12		G	G	G	
FORANE® 22		G	G	G	
ALCOHOLS					
Methyl Alcohol	Pure	G	G	G	
Ethyl Alcohol	Pure	G	G	G	
Butyl Alcohol		G	G	G	
Glycerin	Pure	G	G	G	P
Glycol		G	G	G	P
Benzyl Alcohol		L	P	P	P
ALDEHYDES AND KETONES					
Acetone	Pure	G	G**	L	P
Acetaldehyde		G	L	P	
Formaldehyde	Technical	G	L	P	
Cyclohexanone		G	L	P	
Methylethylketone		G	G	L	P
Methylisobutylketone		G	G	L	P
Benzaldehyde		G	L	P	
CHLORINATED SOLVENTS					
Methyl Bromide		G	P		
Methyl Chloride		G	P		
Trichloroethylene		L	P		
Perchloroethylene		L	P		
Carbon Tetrachloride		P			


CHEMICAL AGENT	CONCENTRATION (100%)	PERFORMANCE			
		20°C	40°C	60°C	90°C
CHLORINATED SOLVENTS CONTINUED					
Trichloroethane		L	P	P	P
PHENOLS					
Phenols		P	P	P	P
VARIOUS ORGANIC BODIES					
Anethol		G			
Glycol Chlorhydrine		P	P		
Ethylene Oxide		G	G	L	P
Carbon Sulphide		G**	L*	P	
Furfural		G	G**	L	P
Tetraethyle Lead		G			
Glucose		G	G	G	G
SALTS, ESTERS, ETHERS					
Methyl Acetate		G	G	G	
Ethyl Acetate		G	G	G	
Butyl Acetate		G	G	G	L
Amyle Acetate		G	G	G	L
Tributyl Phosphate		G	G	G	L
Tricresyl Phosphate		G	G	G	L
Diocetyl Phosphate		G	G	G	L
Diocetyl Phtalate		G	G	G	
Sulfuric Ether		G			
Fatty Acid Esters		G	G	G	G
Methyl Sulfate		G	L		
MISCELLANEOUS PRODUCTS					
Coal Gas		G	G		
Oil		G	G	G	G
Grease		G	G	G	G
Beer		G			
Wine		G			
Fruit Juice		G	G		
Regular Grade Gasoline		G	G	G**	
Premium Grade Gasoline		G	G	G**	
Naphtha Solvent		G	G	G**	
Kerosene		G	G	G**	
Crude Oil		G	G	G**	
Milk		G	G	G	G
Cider		G			
Stearine		G	G	G	
Mustard		G			
2,4-D Lindane		G			
Oxyquinoline (Agricultural Spray)		G			
Turpentine		G	G	G**	
Soap Cleanser		G			
Vinegar		G			
Linseed Cake		G	G	G	G




Permeability

Multi-material solutions are available for applications requiring low or very low permeability. These multilayer solutions maintain the key physical and chemical properties of Rilsan® PA11 in finished components. As a general rule, Rilsan® PA11 offers better barrier properties to gases and liquids than other flexible thermoplastics or rubbers. In particular, it is twice as impermeable to fuels and hydrocarbons versus PA12.

**Permeability of Various Polymers to Natural Gas
(85% C₄H-8% C₂H₆-3% C₃H₈-2% C₄H₁₀) at Different Temperatures**

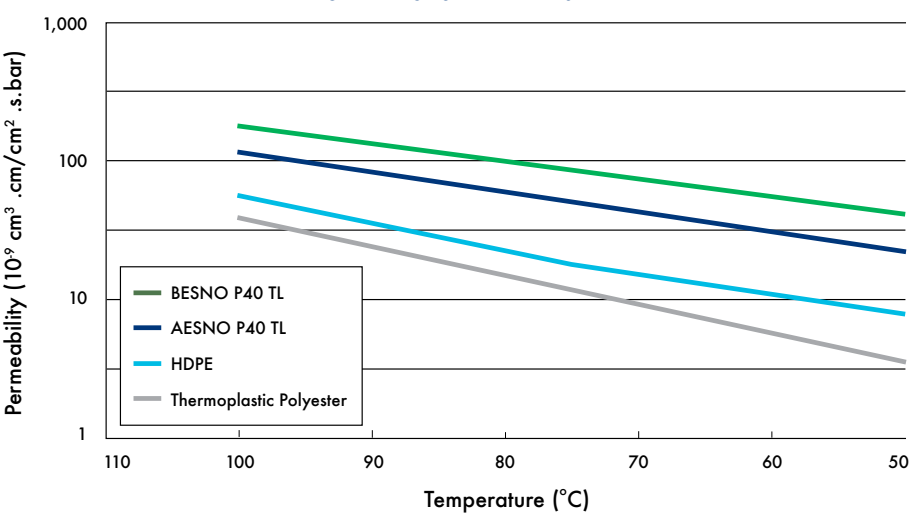

**Permeability of Rilsan® BESNO P40 TL to Various Gases
and at Different Temperatures**

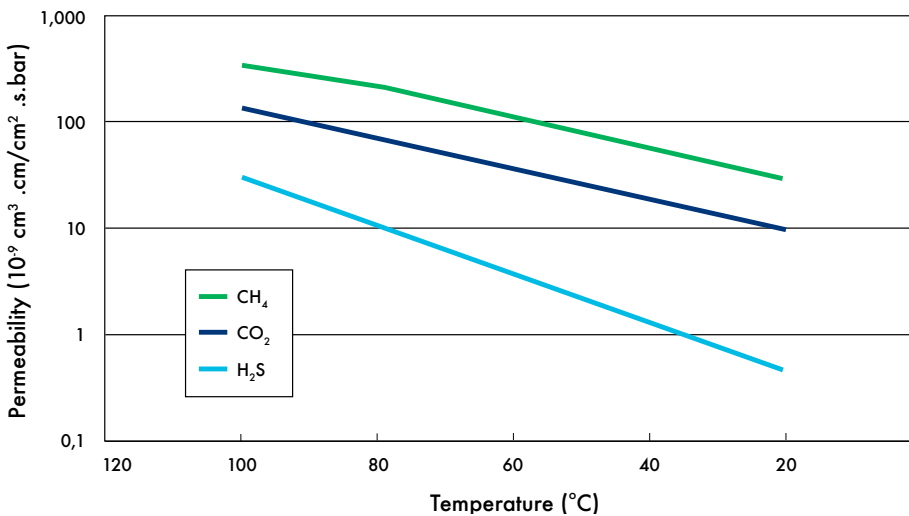



The following tables feature the permeability to various gases of various Rilsan® grades at 20°C.

Rilsan® BESNO TL

GAS	PERMEABILITY (10 ⁻⁹ cm ³ .cm/cm ² .s.bar)
H ₂	7
N ₂	0.15
O ₂	2
CO ₂	7
CH ₄	0.15

Rilsan® BESNO P40 TL


GAS	PERMEABILITY (10 ⁻⁹ cm ³ .cm/cm ² .s.bar)
H ₂	15
CO ₂	6
H ₂ O	0.04
H ₂ S	30
CH ₄	0.6
C ₂ H ₄	2.3
C ₃ H ₈	0.75
C ₄ H ₁₀	5.4

Rilsamid® (PA12) AESNO P40 TL

GAS	PERMEABILITY (10 ⁻⁹ cm ³ .cm/cm ² .s.bar)
CH ₄	1.6
CO ₂	12

Rilsan® PA11 also offers very low permeation to fuels compared to rubber. The following table compares the fuel permeability of tubing made from Rilsan® BESNO P40 TL, versus plasticized PVC and rubber.

PRODUCT	DIMENSION OF PIPE		PERMEABILITY (g/m ² .day)	
	INNER DIAMETER (mm)	THICKNESS (mm)	20°C	40°C
RILSAN® BESNO P40 TL	6	0.5	2	4
PLASTICIZED PVC	6	2	60	120
RUBBER	6	3	60	120

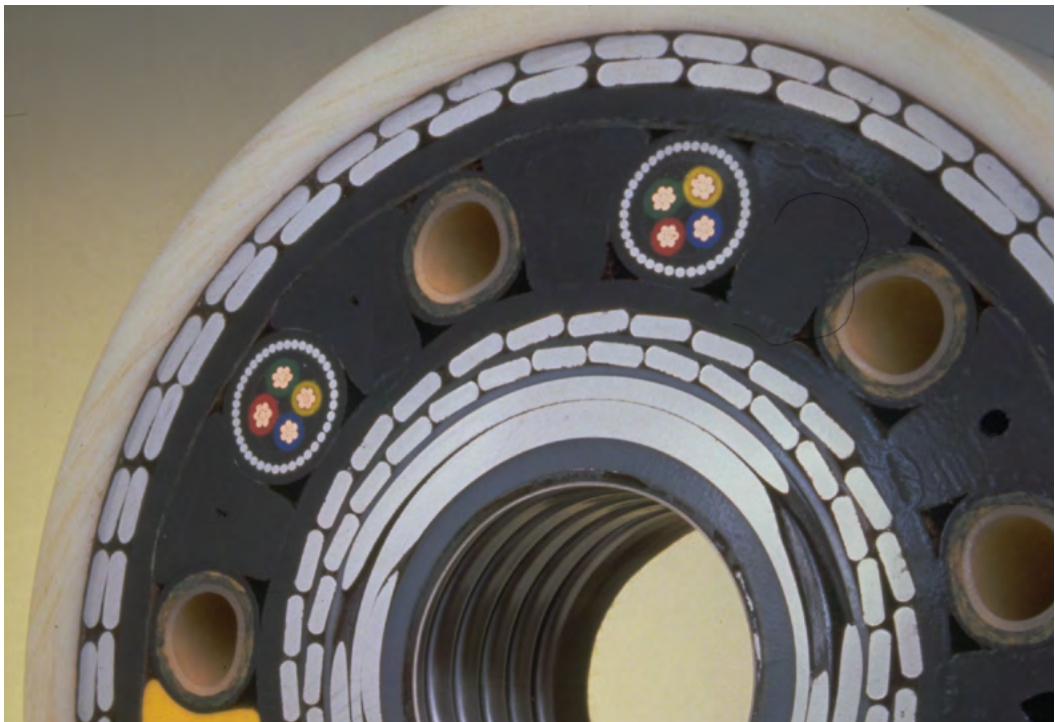

PROCESSING

With a relatively low melting temperature, good melt fluidity, and a high speed of recrystallization, Rilsan® PA11 is well-suited to a wide range of processing technologies: extrusion, extrusion-blow molding, injection molding, injection-blow molding, rotomolding, and 3D printing. To ensure optimum suitability for each of these processing technologies, Rilsan® PA11 is available in a wide range of viscosities.

Rheological Properties


The rheological properties of molten Rilsan® PA11, reflecting their flow capacity, are measured using two types of parameters:

- Melt Volume Index (MVI)
- Melt Viscosity

Melt Volume Index (MVI)

The melt volume index is measured per ISO 1133; it corresponds to the quantity of material at 235°C that can flow in 10 minutes through a 2 mm diameter die under a 2.16 kg load. The melt volume index provides a specific image of the viscosity at a given temperature and shear rate. MVI also depends upon moisture content.

Comparative Melt Volume Indices of Various Rilsan® PA11 Grades, Per ISO 1133 Standard

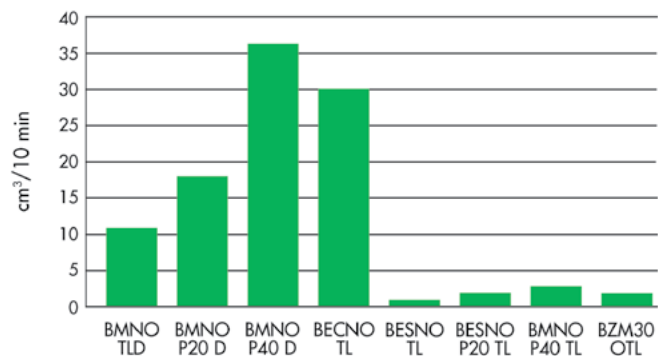


Melt Viscosity

The rheological behavior of Rilsan® PA11 can be measured more accurately with capillary rheometer equipped with tooling having an L/D ratio of 20. As illustrated in the following diagrams, the viscosity of Rilsan® PA11 varies according to shear rate and temperature.




Rilsan® PA11 Grades for Pipe Extrusion

Melt Viscosity of Rilsan® BESNO TL and BESNO P40 TL at 260°C

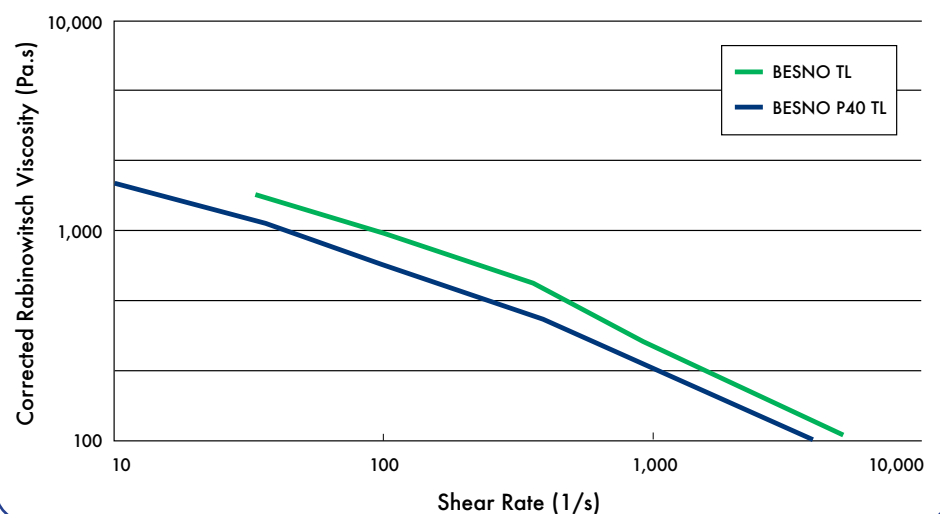




Melt Viscosity of Rilsan® BMNO TLD at 220°C / 240°C / 260°C

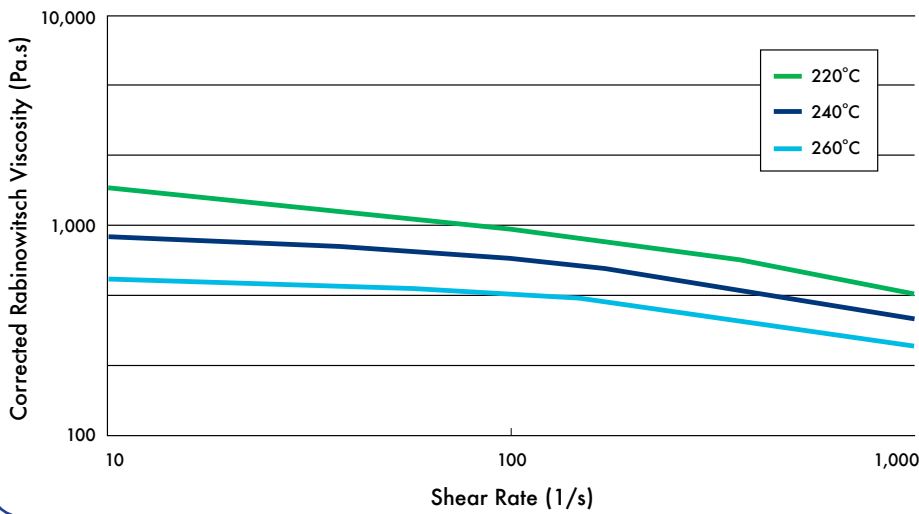


Standard Viscosity Rilsan® PA11 Grade for Injection Molding

Melt Viscosity of Rilsan® BMNO P20 D at 220°C / 240°C / 260°C

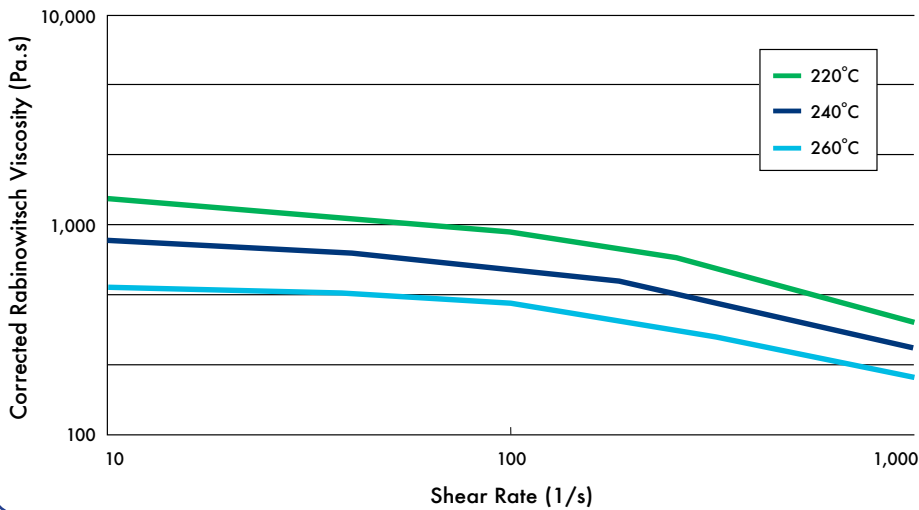

Rilsan® PA11 Plasticised Grade for Injection Molding

Melt Viscosity of Rilsan® BZM30 TL at 220°C / 240°C / 260°C

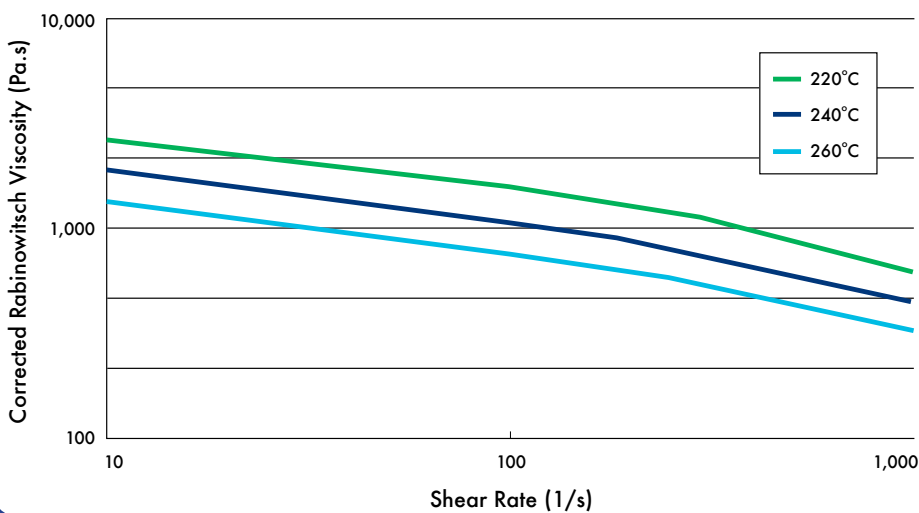

Reinforced Rilsan® PA11 Grade for Injection Molding




Preparation of Rilsan® PA11

Rilsan® PA11 grades are supplied in the form of granules in moisture-proof sealed bags or octabins. Rilsan® PA11 granules do not require pre-drying before use. However, if the packaging has been left open and exposed to air for more than two hours, the product will need to be re-dried under specific conditions (see below for drying conditions).

Moisture Pick-up of Rilsan® PA11

Due to its chemical structure, Rilsan® PA11 has lower moisture pick-up than short-chain polyamides (e.g. PA6, PA66). This low water absorption leads to excellent dimensional stability and causes only minimum variations in its mechanical and electrical properties. Rilsan® PA11 is produced by the polycondensation of amino acid. As a result, it undergoes an equilibrium reaction with water as shown by the following simplified formula:

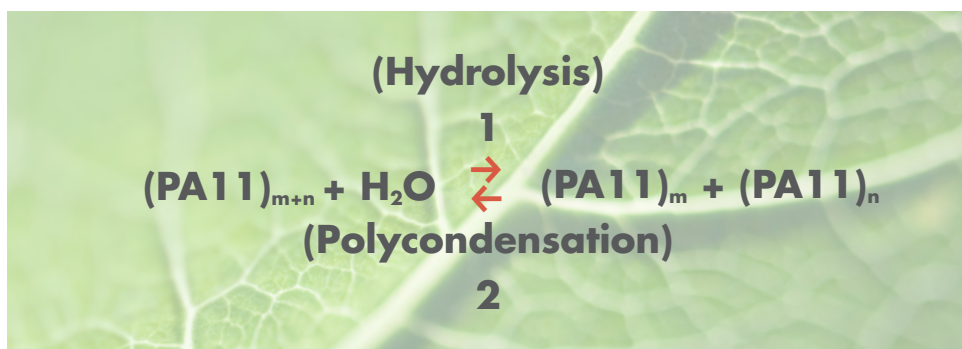

The presence of excess water promotes hydrolysis by reducing the length of the molecular chains. This change will result in a significant drop in mechanical properties but may not always be evident in the form of surface blemishes such as frosting or bubbles.

Since excess moisture can pose problems during the processing of Rilsan® PA11, it is important for the granules to be kept dry at all times. Necessary precautions should be taken to prevent any moisture pick-up during processing.

Drying Conditions

To prevent moisture pick-up, Rilsan® PA11 should first be brought up to the temperature of the plant to prevent any condensation of the ambient moisture as the bags are opened. Additionally, it is essential for the product to be processed within two hours of opening the bag. If either of these conditions are not fulfilled, Rilsan® PA11 granules should be vacuum-dried for at least 4 hours at a temperature between 80°C and 90°C. The migration speed of the moisture to the surface of the granules determines drying time. Raising the temperature does not significantly reduce drying time and presents a risk of oxidation.

Storage

After drying, the granules should be stored immediately in sealed containers, which should be filled to the maximum to keep the pellet/air ratio to a minimum. The size of storage containers should correspond to the equivalent of 2 hours operation in the molding machine.


Coloration

An extensive range of colors can be achieved with Rilsan® PA11. Increasingly processors are required to produce their own color using masterbatches in order to fulfill specific needs or to reduce stocks of colored product. This normally requires adjustments to the injection-molding machine (e.g. plastification time, rotation of the screw, back pressure, use or otherwise of mixing adapter).

Recycling

The recycling of scraps requires a number of best practices in order to prevent contamination during the various storage and grinding phases. As long as the material is free of all traces of oxidation and contamination, it is possible to recycle it in any production process that does not specifically require 100% virgin product. The proportion of recycled material should be adjusted on the basis of the mechanical properties of the end component, but generally should not exceed 20% by weight.

Moisture Pick-up of Rilsan® PA11 Based on Exposure Time to Air (at 20°C – 65% R.H.)

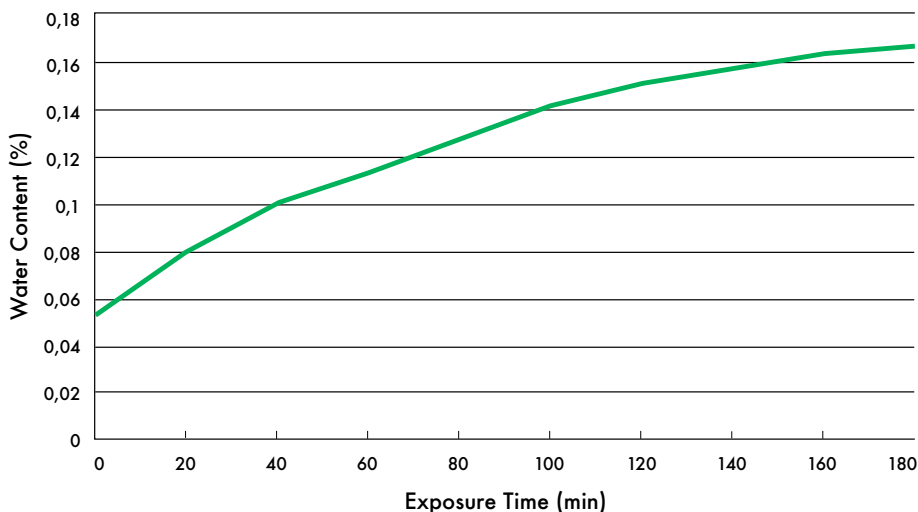



Recycling product requires specific precautions to prevent drop-off in performance or changes of the color or the appearance of the component. Our technical team will be pleased to assist you further in this regard.

Processing Rilsan® PA11

Injection Molding

With its melt flow characteristics, Rilsan® PA11 is suited for injection molding using commercially available equipment.

Injection Unit

SCREW

Standard screws are suitable for Rilsan® PA11. These screws consist of 3 zones with a non-return valve. The length of the screw should be at least 1.5 times its diameter, with a minimum compression ratio of 2.5.

INJECTION NOZZLE

The high melt fluidity of Rilsan® PA11 requires the use of a shut-off nozzle. If this is not fitted, molten polymer will leak out between injection cycles, thereby producing visible blemishes on the finished article (oxidation, cold slug, flow break, etc.).

Mold Temperatures

The use of temperature-regulated tooling is highly recommended for the injection molding of Rilsan® PA11. By controlling mold temperatures, processors can affect the appearance of the finished article, the ease of filling, mold release, and shrinkage. Except for a few specific cases, Rilsan® PA11 grades require cold molds (30 to 40°C). However, when injection molding thin-walled articles, or with large surface areas or intricate shapes, higher temperatures can be used to fill the mold cavity more easily. Glass fiber-reinforced grades require hot molds (90 – 100°C) to produce an even and glossy surface finish.

Injection Temperatures

Whichever Rilsan® PA11 grade is used, the temperature should rise from the upstream feed zone to the downstream zone to produce a sufficiently homogeneous melt.

RILSAN® PA11 GRADES	TEMPERATURE (°C)			
	HOPPER	CENTRAL SECTION	OUTLET	NOZZLE
BMN	210	225	240	230
BZM30	240	260	270	270

The outstanding thermal stability of Rilsan® PA11 allows much higher temperatures to be used (up to 300°C). However, these temperature levels should be used only when needed.

Shrinkage of Rilsan® PA11

Understanding and controlling shrinkage is key for producing high quality molded parts. Shrinkage is defined as the dimensional variation between the cold mold and the cooled molded part measured after 24 hours. It is normally expressed as a percentage of the mold dimensions. The various parameters which can affect shrinkage are as follows:

- Design of the article, location and dimension of feed system
- Injection pressure and holding pressure
- Effective duration of holding pressure (before threshold setting)
- Mold temperature and cooling time
- Temperature of the material injected
- Injection speed

HOLDING PRESSURE AND TIME	SHRINKAGE
TEMPERATURE OF THE MOLD	SHRINKAGE
TEMPERATURE OF THE MATERIAL	SHRINKAGE
COOLING TIME	SHRINKAGE
INJECTION SPEED	SHRINKAGE

An evaluation of the shrinkage of Rilsan® BMNO (standard molding grade) and Rilsan® BZM30 (glass fiber reinforced molding grade) was conducted on injected test samples with thicknesses of 2, 4, and 6mm, while maintaining an injection threshold equal to 25% of the nominal thickness (0.5mm layers for a 2mm sheet). Shrinkage, measured 24 hours after mold release and after thermal treatment, was determined from the following two measurements:


- Shrinkage R, in flow direction
- Shrinkage R', perpendicular to flow direction.






Rilsan® BESNO TL


Shrinkage R, 24 h After Removal From Mold

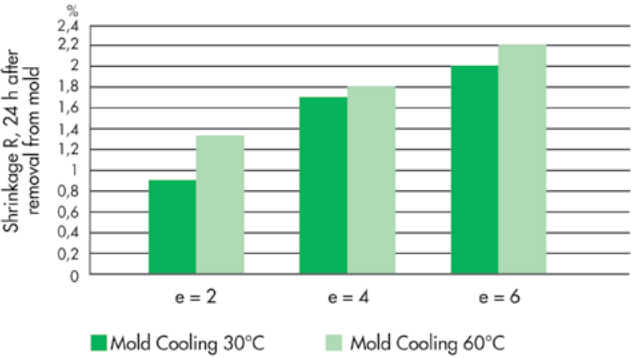


Shrinkage R', 24 h After Removal From Mold

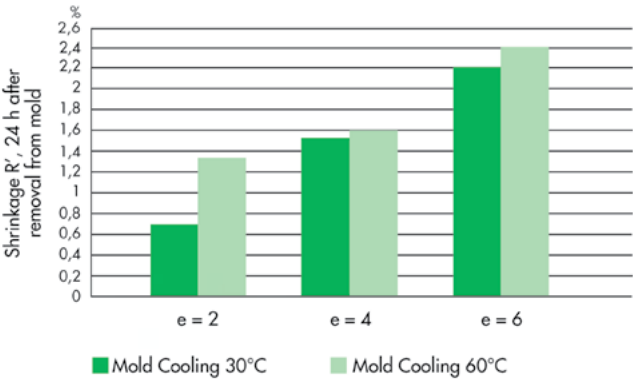

Shrinkage R, After Thermal Treatment

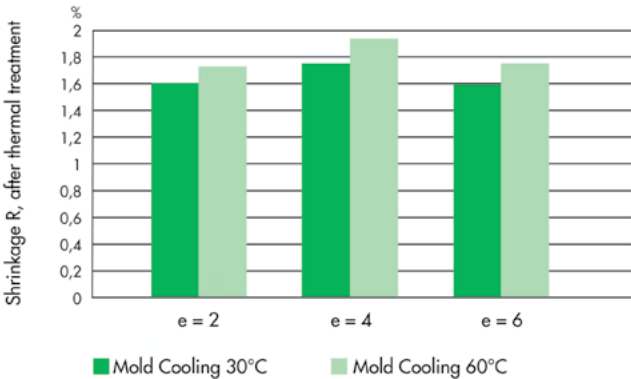


Shrinkage R', After Thermal Treatment

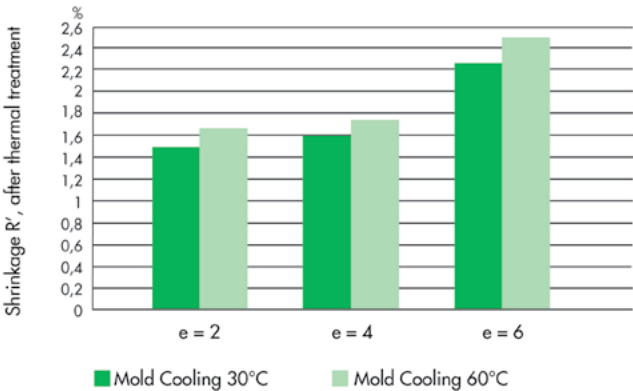




Rilsan® BESNO TL


Shrinkage R, 24 h After Removal From Mold

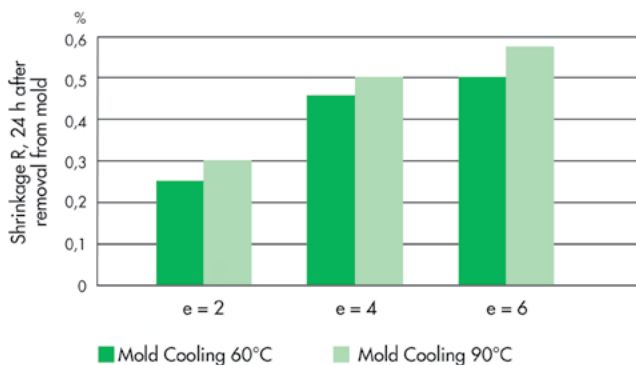


Shrinkage R', 24 h After Removal From Mold

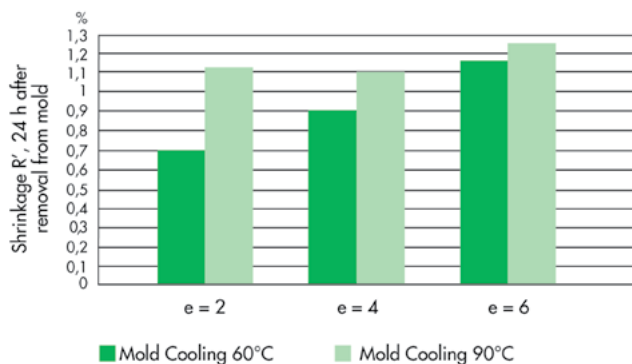

Shrinkage R, After Thermal Treatment

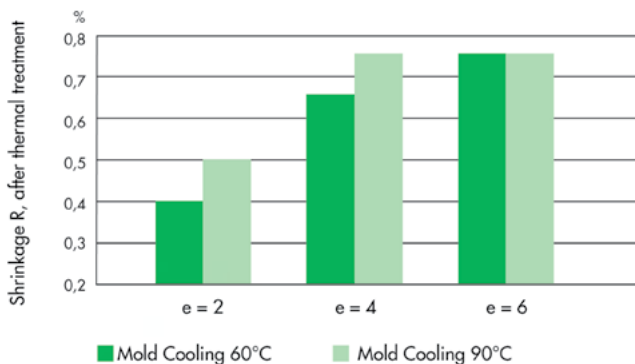

Shrinkage R', After Thermal Treatment

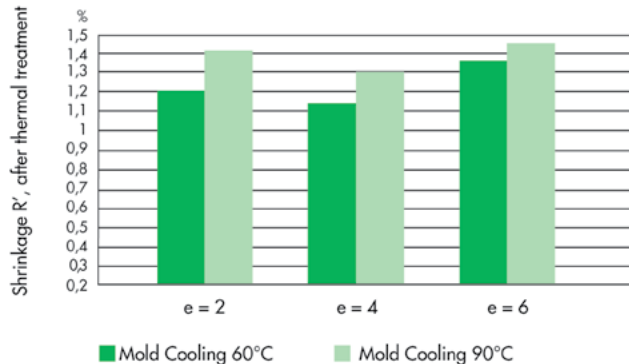

Back-pressure

Rilsan® PA11 can be plasticized easily, and back-pressure is not necessary, however, it is advisable when master-batch coloration is used, as this ensures good dispersion of the colorant.

Injection Pressure and Speed

Injection pressures normally range between 400 and 700 bars for Rilsan® PA11 non-reinforced grades and between 700 and 1000 bars for reinforced grades. The choice of value will generally be determined by the processor on the basis of other factors such as temperature of the material and the mold. Where possible, it is

recommended to use lower pressure and higher temperatures to achieve optimum properties for articles molded from Rilsan® PA11.

NOTE

In the case of unfilled grades, shrinkage 24 hours after removal from the mold occurs preferentially in the direction of the melt flow, which is also the main direction of the fibers, hence $R > R'$. The presence of oriented fibers generally limits shrinkage following the melt flow, whilst increasing shrinkage across the flow, hence $R' > R$. Even though these effects are generally acceptable for fiber-reinforced

polymers, they depend to a large extent on the thickness of the article (skin effects), the degree of orientation of the fibers (anisotropic) and their length, and the type of feed and geometry factors.



Extrusion (Film and Pipe)

For extrusion, it is essential to use Rilsan® PA11 granules with a moisture level below 0.1%, to prevent bubbles and other defects in the wall section, and to ensure a steady feed of the granules and a constant mechanical energy absorbed by the material.

Screw: Functions and Profiles

Screws suitable for the processing of Rilsan® PA11 should fulfill the following functions:

- Consistent feed of granules
- Efficient melting and de-gassing of the product
- Homogenization of the melt through sufficient back-pressure

Screws with a long compression zone help minimize variations in the pressure reached at the end of this zone and any resulting variations in the flow rate. Together with the compression rate, the clearance between the screw and the barrel is the most important parameter when choosing the right screw for Rilsan® PA11.

Temperature Profile

The specific temperature profile required can vary considerably from one machine to another. The following information is therefore given as an indication. It will also depend on the extrusion speed and the Rilsan® PA11 grade chosen, i.e. whether lubricated or not. For example, non-lubricated grades require higher temperatures, especially in the first zone of the extruder.

GRADES	TEMPERATURE (°C)					
	HOPPER	FEEDING ZONE	COMPRESSION ZONE	METERING ZONE	EXTRUSION HEAD	DIE
BESNO P40 TL	60	175	220	235	230	220
BESNO P20 TL	60	180	225	240	230	220

Extrusion of Rilsan® PA11 Tubing

The extrusion of Rilsan® PA11 tubing requires a water tank whose two main functions are to form the shape of the tube in a calibrator under vacuum and to efficiently cool the pipe through continuously circulating water in the tank. The level of vacuum can be varied from 50 to 400 mbars and is used to adjust the outer diameter of the tube. Rilsan® PA11 features unique extrusion properties versus PA12, due to its viscosity kick during the extrusion process. This is a key benefit for large diameter extrusion where its melt strength is a real advantage.

Rotomolding

The rheological properties (fluidity) of Rilsan® PA11 make it suitable for applications using the rotomolding technique and in particular the manufacture of articles which include metal inserts. Rotational molding does not induce residual stress in the material such as that found in injection molded articles. This is because during the rotomolding process, the material is not subject to mixing or compacting to the same degree as in an extrusion screw or an injection molding machine. Rotomolding is also suitable for articles with a more intricate design or with larger dimensions than those produced by injection molding.

Mold Technology

The rotomolding of specific Rilsan® PA11 grades requires molds of a traditional construction (steel, aluminum, copper plate, etc.). It is also important for vents to be present. Although removing Rilsan® PA11 articles from the mold is easy, it is advisable, where problems do occur, to treat the surface of the mold cavity, either by applying a fluorinated coating or a thermoset varnish, or by spraying the walls of the mold cavity with silicone or similar products.

Heating temperature and duration
To achieve optimum rotomolding of Rilsan® PA11 articles, it is recommended to heat the product to between 260°C and 300°C. The duration of the heating is governed by the temperature of the oven, the thickness and thermal conductivity of the mold, and the required Rilsan® PA11 thickness.

Rotation Speed

The mold rotation speed along the two axes is based on the dimensions and design of the mold. The choice of these parameters governs the consistency of the material thickness. They should be determined on a case-by-case basis.

Cooling

This obeys the same parameters as heating time (temperature of air and water, thermal conductivity and thickness of the mold). In order to prevent distortion or surface defects on the articles, the temperature should not be allowed to drop too quickly in the first phase. For this reason, preliminary cooling with air is advisable. An air-water-air cooling cycle typically gives the best results and it ensures longer life for the molds by preventing excessively sudden thermal shocks.

Converting Semi-finished Products

Machining

Rilsan® PA11 is suitable for the various machining processes: drilling, tapping, sawing, milling, turning, grinding, and polishing. It is available on the market in the form of semi-finished products such as profiled bars, pipes, sheets and rough mold blocks. Heating up the part should be avoided during machining.

Coloration

Rilsan® PA11 is highly suitable for coloration using a number of methods: in the matrix (i.e. during the production of the polymer), through the addition of pigments, by using masterbatches, or by liquid colorants. Contact the Arkema's technical service team for recommendation of the most suitable colorants for PA11.

Multi-material structures

Arkema offers a wide range of glues, adhesives and tie layers, making the company a world leader for the design of multi-material, multi-layer structures. Bostik, a global leader in adhesives is also a subsidiary of the Arkema Group.

Bonding

Rilsan® PA11 can be bonded using either polymeric resins or adhesives onto virtually any type of substrate (e.g. wood, paper, cement, leather, glass, thermosets, thermoplastic resins).

Welding

Rilsan® PA11 can be welded using a wide variety of techniques: high frequency, induction, friction, and ultrasonic welding.

Other Techniques For Assembling Multi-materials

Rilsan® PA11 can be combined with many other thermoplastics or materials by insert-molding, over molding, co-extrusion, etc.

Bio-based, Renewable Solutions

Arkema is a world leader in ultra high performance polymers that are bio-based/renewable. For over 70 years, Arkema has been a leading innovator in both monomer and polymer production from castor oil feedstock. The Group is well known for its flagship amino 11 chemistry and the Rilsan® PA11 and Pebax® Rnew® polymer ranges. Arkema is also a world leading supplier of bio-based sebacic acid (DC10) and derivative monomers (DA10) as well as complementary renewable PA610 (Rilsan® S) and PA1010 (Rilsan® T) polymer ranges.

Sustainably Sourced

The bean from the castor plant has a number of advantages as a sustainable feedstock:


- It generally does not compete with food. The castor bean provides little nutritional value for humans or animals. Almost all of its downstream values are in industrial applications.
- It grows in semi-arid to sub-tropical regions, often in remote locations where little else can sustainably grow.
- The bean is non-GMO.
- The castor plant requires very little irrigation and is naturally pest and drought resistant.

Arkema is a member of the Pragati initiative in India, a cooperative project with BASF, Jayant Agro, and the NGO Solidaridad. Pragati encourages and educates local farmers on sustainable and responsible castor plant farming.

Global Service

Arkema's Technical Polymers division boasts a global and integrated organization in terms of production, technical support, and development. At every stage of a project involving the use of Rilsan® PA11 (design, industrial development, market launch), the Technical Polymers division will be pleased to provide you with any assistance you may require. Our technical teams specialized in high-performance polyamides can help in grade selection, processing parameters, application development, and much more. Finally, as a long-standing partner to high-tech industries (oil and gas, aerospace, automotive, industrial vehicles, electronics etc.), the Technical Polymers division can oversee complex developments involving the end-user and the industrial supply chain (processors and OEMs).



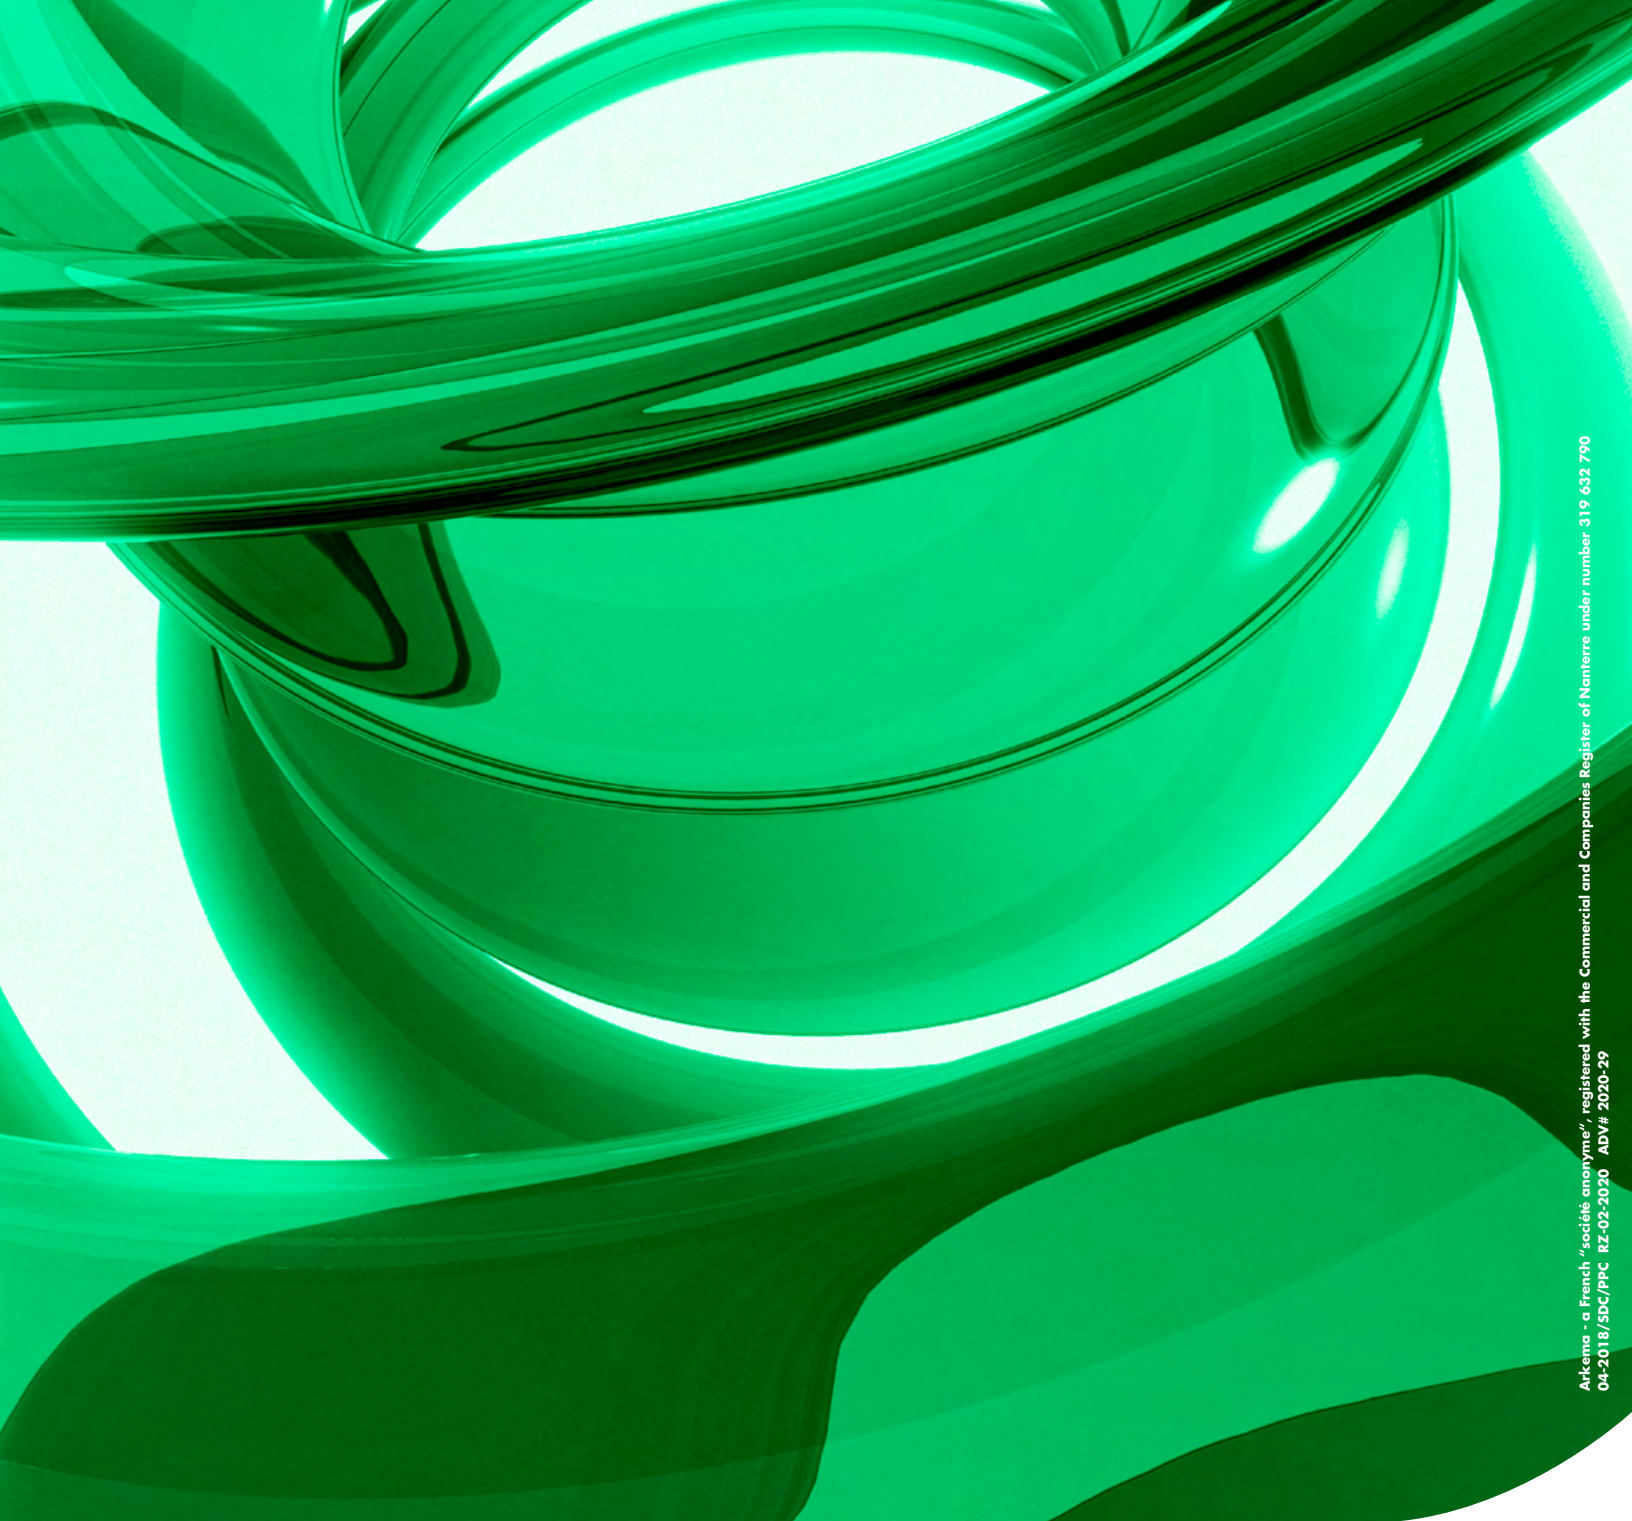

Please consult Arkema's disclaimer regarding the use of Arkema's products at
<http://www.arkema.com/en/products/product-safety/disclaimer/index.html>

Pebax®, Rilsan®, Rilsamid® and Rnew® are registered trademarks of Arkema.
© 2020 Arkema Inc. All rights reserved.

extremematerials-arkema.com
rilsan.com

Contact Information

China: +86 21 61476888
Japan: +81 3 5251 9900
Korea: +82 2 37036700
Singapore: +65 64199199
Taiwan: +886 2 27476979
India: +91 22 66137500

Arkema Inc. (Americas)

900 First Avenue
King of Prussia, PA 19406
Tel.: +1 610 205 7000
Fax: +1 610 205 7497
arkema-americas.com

Headquarters: Arkema France

420, rue d'Estienne d'Orves
92705 Colombes Cedex - France
Tel.: +33 (0)1 49 00 80 80
Fax: +33 (0)1 49 00 83 96
arkema.com

ARKEMA
INNOVATIVE CHEMISTRY